

# NEW MAGNETS FOR THE IR: HOW FAR ARE WE FROM THE HL-LHC TARGET? \*

GianLuca Sabbi (LBNL) for the LARP collaboration

## *Abstract*

Insertion quadrupoles with large aperture and high gradient are required to upgrade the luminosity of the Large Hadron Collider (LHC). The US LHC Accelerator Research Program (LARP) is a collaboration of US DOE National Laboratories aiming at demonstrating the feasibility of Nb<sub>3</sub>Sn magnet technology for this application. Several series of magnets with increasing performance and complexity have been fabricated, with particular emphasis on addressing length scale-up issues. Program results and future directions are discussed.

## INTRODUCTION

Replacing the first-generation IR quadrupoles with higher performance magnets is one of the required steps for the High-Luminosity LHC [1]. Although designs based on NbTi conductor are being considered, the intrinsic properties of Nb<sub>3</sub>Sn make it a strong candidate to meet the ultimate performance goals in terms of operating field, temperature margin, and radiation lifetime. Under typical upgrade scenarios, the new magnets will provide increased focusing power to double or triple the luminosity, and at the same time will be able to operate under radiation loads corresponding to a 10-fold increase in peak luminosity, and with radiation lifetime consistent with a 3000 fb<sup>-1</sup> integrated luminosity goal.

Starting in 2004, the LHC Accelerator Research Program (LARP) collaboration has led the US effort to develop Nb<sub>3</sub>Sn quadrupole magnets for the LHC luminosity upgrade [2]. The program is founded on the knowledge base and infrastructure of the DOE General Accelerator Development programs at BNL, FNAL and LBNL. With respect to these programs, it provides specific focus and resources to select the best available technologies for the luminosity upgrade and bridge the gap from proof-of-principle models to fully developed prototypes incorporating all features required for operation in the LHC accelerator. Significant progress has been made to date and the program is well positioned to complete the technology demonstration by 2014 and initiate a construction project. A successful luminosity upgrade based on Nb<sub>3</sub>Sn is expected to open the way to a number of other applications, both within and beyond high energy physics.

## HIGH FIELD MAGNET TECHNOLOGIES

Excellent mechanical and electrical properties of multi filamentary NbTi have made it the conductor of choice in all superconducting accelerators to date. However, the intrinsic properties of NbTi limit its field reach in accelerator applications to about 8 T. In order to surpass this threshold, superconductors with higher upper critical field are needed. Niobium-Tin (Nb<sub>3</sub>Sn) is currently the most advanced material available. It carries current densities similar to NbTi at more than twice the field, and is available in long lengths with uniform properties. Nb<sub>3</sub>Al offers lower strain sensitivity with respect to Nb<sub>3</sub>Sn, but its manufacturing process is not sufficiently well developed to support magnet fabrication. The low-temperature properties of HTS materials such as Bi-2212 are far superior to both Nb<sub>3</sub>Sn and Nb<sub>3</sub>Al. However, many technology challenges need to be addressed before practical designs based on these materials can be developed and implemented in prototypes.

All superconductors suitable for high field applications are brittle and strain sensitive, requiring new approaches to magnet design and fabrication to complement or replace those established for NbTi. In particular, because of their brittleness, high field superconductors cannot be drawn to thin filaments like NbTi, but have to be formed in the final geometry by high-temperature heat treatment. In the fully reacted state, the filaments are extremely sensitive to strain. Therefore, attempting to wind pre-reacted cables in accelerator-type coils would result in unacceptable critical current degradation at the ends. Instead, coils are wound using un-reacted cable, when components are still ductile, and the superconductor is formed by high temperature heat treatment after coil winding. This technique requires the use of insulation and coil structural components that can withstand the high reaction temperatures. In addition, new approaches to mechanical support and quench protection are required to safely handle reacted coils through magnet assembly, cool down and excitation.

A significant and sustained R&D effort is required to develop technologies that can take advantage of the properties of high field superconductors while coping with the associated challenges. Early work on Nb<sub>3</sub>Sn accelerator magnets was performed at BNL [3], CEA [4], CERN [5-6], and LBNL [7]. In the mid-90s, the dipoles MSUT (Twente University) and D20 (LBNL) reached fields of 11-13 T [8-9]. More recently, the LBNL dipoles RD3-B and HD1b achieved record field of 14.7 T and 16.1 T, respectively, using simple racetrack coil designs

\* This work was supported by the Director, Office of Energy Research, Office of High Energy and Nuclear Physics, High Energy Physics Division, U. S. Department of Energy, under Contract No. DE-AC02-05CH11231.

[10-11]. The LARP program was established to build on this base and develop the technology to a mature state, consistent with the requirements of the High-Luminosity LHC project.

## THE LARP PROGRAM

### Goals and organization

LARP was established in 2004 to enable active participation of the U.S. scientific community in the accelerator research program of the LHC machine. While the program scope included accelerator commissioning and operation, special emphasis was given to the development of magnet technologies relevant to the LHC luminosity upgrade, consistent with the physics priorities established by the US HEP advisory panel [12]. LARP is also intended to serve as a vehicle to advance collaboration among US Laboratories as well as international cooperation in large science projects.

The documents that initiated the program identified its key goals, to be achieved in close collaboration with CERN:

- Help the LHC achieve its design luminosity quickly, safely and efficiently.
- Continue to improve LHC performance by advances in understanding and the development of new instrumentation.
- Use the LHC effectively as a tool to gain a deeper knowledge of accelerator science and technology.
- Extend LHC as a frontier High Energy Physics instrument with a timely luminosity upgrade.

LARP was firmly established as an advanced R&D program, which would help the US HEP community in maintaining a leadership role in accelerator technology, and set the basis for a separately funded construction project. “Preparing to build the next generation hadron collider” was also explicitly mentioned among the key program goals in the LARP proposal (Fig.1).

Deliverables Goals	Hardware Commissioning	Beam Commissioning	Fundamental Accelerator Research	Instrumentation & Diagnostics	Magnet R&D
Maximize HEP at the LHC	Y	Y	Y	Y	
Improve LHC Performance			Y	Y	
Advance Accelerator Science/Technology			Y	Y	Y
Expand LHC HEP by a Timely Upgrade			Y	Y	Y
Prepare to build the Next Generation Hadron Collider	Y	Y	Y	Y	Y

Fig. 1: LARP goals and deliverables matrix [2]

The program is organized in three sections: (i) accelerator systems, (ii) magnet systems and (iii) programmatic activities. The accelerator systems section includes the

development of advanced instrumentation and collimation systems, as well as accelerator physics studies. The magnet systems section is focused on the development of Nb<sub>3</sub>Sn interaction region quadrupoles, and is described in detail in this paper. The programmatic activities section manages the long term visitor program and the Toohig post-doctoral fellowship.

### Magnet program components

The LARP magnet program was conceived as a progression of studies and technological steps, starting from simple systems designed to address specific R&D issues, and building toward more complex configurations incorporating all required features for operation in the accelerator. The program organization reflects this approach and has evolved in time to adapt to the different stages of the R&D. The main areas, corresponding to “level 2” categories in the work breakdown structure, are:

- Materials R&D, including: strand specifications, procurement and characterization; cable fabrication, insulation and qualification; coil heat treatment optimization and verification.
  - Technology development with racetrack coils. This area was a key component of the program from its inception until 2008. Through the Sub-scale Quadrupole (SQ) and Long Racetrack (LR) models, it addressed fundamental issues of conductor performance, mechanical analysis, instrumentation, quench protection, and most notably, scale-up of coil and structures to 4 m length, paving the way to the Long Quadrupole program.
  - Design studies: This area was also very active in the first part of the program, to select the most promising designs for future model quadrupoles, compare different IR layouts, and perform supporting studies in areas such as radiation deposition and field quality. While the program has progressively shifted toward experimental demonstrations, renewed focus in this area is developing in connection with the HL-LHC design study [13].
  - Model quadrupoles: this area oversees the detailed design, fabrication and testing of short quadrupole models, including the 90 mm aperture Technology Quadrupoles (TQC and TQS) and the 120 mm aperture High Field Quadrupoles (HQ).
  - Long Quadrupoles (LQ), which covers the scale up from 1 m to 4 m length (LQ and LHQ models).
- Each area is organized around tasks with specific goals and milestones. Individual task typically utilize expertise, resources and infrastructure from several laboratories, leading to close collaboration at the level of each activity. This approach may appear less efficient with respect to a project-type organization in which responsibilities for key deliverables are distributed among laboratories, with each group working independently on its portion. However, it has proven extremely valuable in comparing and

integrating the experience and methods developed by different groups, and represented a key element of the program success, both in terms of technical results and from a collaboration standpoint.

### Fabrication and test database


Since its start in 2004, the LARP program has fabricated and tested a large number of models of different designs. This section summarizes the tests performed and the key issues addressed. Progress and issues in each area are summarized in the following section. Figure 2 is a magnet development flowchart showing the LARP model magnets and their progression from technological tests toward accelerator quality designs. The main program components are:

1. Sub-scale Quadrupole - SQ (LBNL, FNAL). SQ is based on four racetrack coils of the LBNL “sub-scale” design [14]. A combination of existing and new coils was used leading to five tests at 4.5 K and two tests at 1.9 K [15-16]. Among the highlights of these tests were:
  - Demonstration of conductor performance up to the short sample limits under conditions similar to those required by the Technology Quadrupoles (field, current, stress) and using the same heat treatment.
  - Detailed 3D finite element modeling and verification of stress calculations against strain gauge measurements.
  - Studies of quench propagation and protection, including temperature and stress limits during a quench.

- Studies of the effect of axial pre-load on the quench performance and training.
- In addition, the SQ tests indicated that block-coil quadrupoles can perform at the expected levels in practical configurations. However,  $\cos(2\theta)$  coils were selected for the LHC IR quad application since design studies showed that they would provide significantly better magnetic efficiency for this application.

2. Sub-scale Magnet - SM (BNL, LBNL). This magnet was used as a technology transfer tool in preparation for the design and fabrication of the long racetrack coils at BNL. Two sub-scale coils were fabricated and assembled at BNL using design, cables, parts, mechanical structure and fabrication procedures provided by LBNL. The magnet was also tested at BNL and achieved its full conductor potential [17].
3. Long Racetrack Shell - LRS (BNL, LBNL). The main goal of LRS was to provide a first demonstration that  $Nb_3Sn$  coils and shell based structures could be scaled to lengths significantly above 1 meter. The coil design was very similar to the sub-scale magnet, with a length increase of more than a factor of ten. The support structure was designed and pre-assembled at LBNL. Two coils were fabricated, assembled and tested at BNL achieving 91% of the short sample limit [17]. Based on feedback from this test, the support structure which originally utilized a one-piece shell was segmented in four sections, leading to further performance improvements (96% of SSL) in the second test using the same coils [18].
4. Technology Quadrupole – TQ (FNAL, LBNL +

Fig. 2: Magnet Development Flowchart

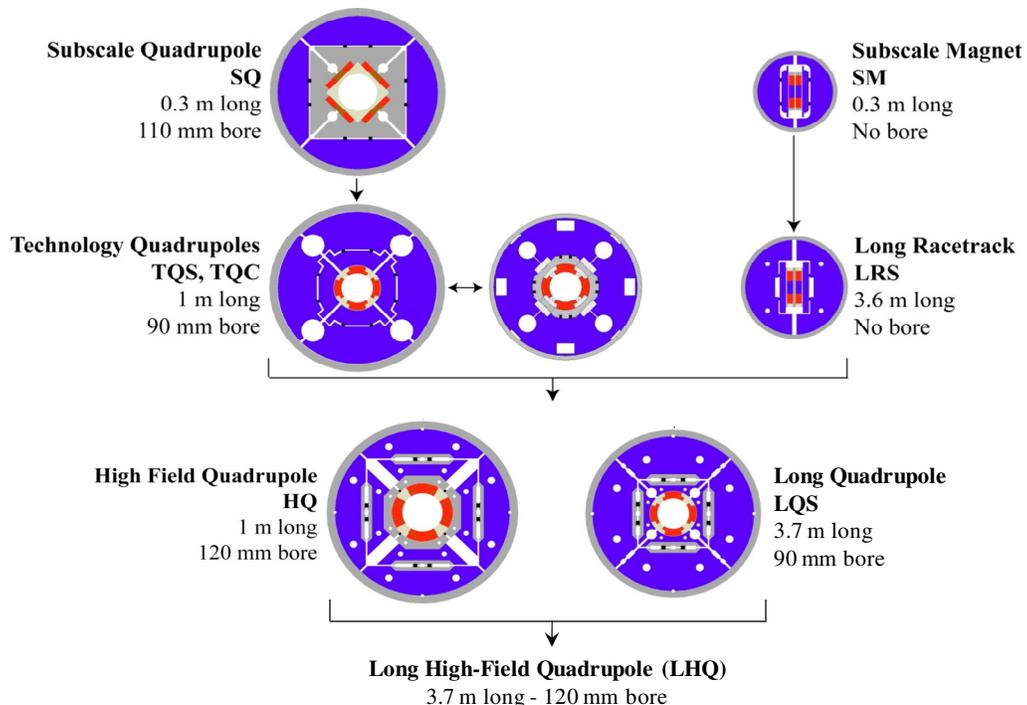

CERN). The TQ models are based on the traditional  $\cos(2\theta)$  coil design with 90 mm aperture and 1 m length. Three generations of coils were fabricated using different wire designs. In total, more than 30 coils were fabricated using a distributed production line, with winding/curing performed at FNAL and reaction/impregnation performed at LBNL. Two support structures were compared, a collar-based structure designed by FNAL and a shell based structure designed by LBNL. About 15 models were tested in a variety of configurations at LBNL, FNAL and CERN [19-20]. Among the main studies and results obtained using the TQ models are:

- Achieved 240 T/m in 90 mm aperture, about 20% higher than the original performance target.
  - Demonstrated robust performance, in particular the capability to transport, disassemble and reassemble coils in different configurations.
  - Performed a systematic investigation of Nb<sub>3</sub>Sn stress limits (engineering design space)
  - Completed a fatigue test involving 1000 cycles from low to high current.
5. Long Quadrupole Shell – LQS (BNL, FNAL, LBNL). LQS is a scale-up of the TQS design from 1 m to 4 m. The development of long Nb<sub>3</sub>Sn quadrupoles was recognized as a key R&D goal from the program outset. In April 2005, LARP, DOE and CERN agreed that achieving a gradient of 200 T/m in a 90 mm aperture, 4 m long quadrupole would serve as a convincing demonstration of such scale-up. The primary purpose of both TQ and LR programs was to serve as a basis for LQ. All three labs participated in the LQ design, fabrication and test activities. The 200 T/m target was achieved during the first test in December 2009 [21]. A second test with optimized preload using the same coils (LQS01b) achieved a 10% increase in performance, to 220 T/m. The next step is the assembly and test of LQS02, using four new coils, to demonstrate reproducibility. A third series of tests is also planned using the latest generation conductor (RRP 108/127).
6. High-Field Quadrupole - HQ (BNL, FNAL, LBNL + CERN). Detailed optics and layout studies of the upgraded LHC insertions indicate that increasing the quadrupole aperture leads to improved performance. Taking into account the space limitations in the tunnel, an aperture of 120 mm was selected for the development of upgraded quadrupole models based on NbTi. In order to explore the technological limits associated with larger aperture, and to provide a direct comparison between NbTi and Nb<sub>3</sub>Sn performance, the same aperture was selected by LARP for the next series of High-Field Quadrupoles. The 120 mm aperture, two-layer coil design using a 15 mm wide cable results in a 15 T peak field and 1.2 MJ/m stored energy, about a factor of 3 higher

than in TQ and LQ. For the first time in LARP, coil alignment features are included at all phases of fabrication, assembly and excitation. To date, 12 coils were fabricated and 3 tests were performed. During the first test [22] the magnet achieved 155 T/m at 4.5 K, well above the intrinsic limit of NbTi at 1.9 K. However, high rates of insulation failures were observed, prompting a revision of the cable and coil design to decrease conductor strain during fabrication. A scale up of the HQ design to 4 m length is planned as a final technology demonstrator.

## R&D PROGRESS AND ISSUES

### *Strand design and fabrication*

Three wire types were utilized in LARP, all produced by Oxford Superconducting Technology (OST):

- Modified Jelly Roll wire with 61 sub-elements, 54 of which contain superconducting filaments while the remaining 7 are made of copper stabilizer (MJR 54/61)
- Rod Restack Processed wire with 61 sub-elements, 54 of which contain superconducting filaments while the remaining 7 are made of copper stabilizer (RRP 54/61)
- Rod Restack Process wire with 127 sub-elements, 108 of which contain superconducting filaments while the remaining 19 are made of copper stabilizer (RRP 108/127)

The MJR wire represents an older generation wire that was already retired from production at the beginning of the LARP program. It was used in the first generation of TQ models since it was available in sufficient quantity to allow a direct comparison of different mechanical structures.

The RRP 54/61 wire was used in the majority of the LARP tests to date. It delivered solid performance allowing the LR, TQ and LQ models to reach their R&D objectives and performance goals. However, this design results in a rather large effective filament size (~70 μm) in the strand diameter of interest (0.7-0.8 mm) leading to stability thresholds which, for moderate field designs such as TQ, are only within a factor of 2 above the operating point. Further erosion of the stability margin may result from conductor degradation due to processing or strain. As a result, performance limitations have been observed at low temperature (1.9K) in second-generation TQ models.

The RRP 108/127 was first procured by LARP in 2007, when it was still considered an R&D wire by OST, to evaluate its performance and encourage further development and transition to the production stage. It provided solid performance in the TQS03 model with no signs of instability, leading to its adoption as a baseline LARP wire starting in 2009. However, due to the long

lead times for procurement and magnet fabrication, the first models to benefit from this transition will only be tested in 2012. In addition, further improvements to the 108/127 design are required to match the average piece length and critical current densities obtained in the 54/61 design. The 5-6 year cycle from initial evaluation to full utilization in the magnet fabrication pipeline indicates that incorporating newer generations of wire (such as RRP 217 or Powder-in-Tube) before the 2015 anticipated start of the IR quadrupole production will be a challenge.

### *Cable design and fabrication*

Although the fabrication of Nb<sub>3</sub>Sn cables was already well established at the start of the program, LARP provided an opportunity for larger scale manufacturing, further optimization and detailed characterization. To date, more than 7 km of cable of three different designs were fabricated with minimal losses. The current R&D effort is focusing on transitioning from a three-step process (involving a first cable fabrication pass at larger size, followed by anneal and re-roll to final size) to a one-step process using pre-annealed strand. The one-step process is expected to be more robust and efficient, and is more compatible with the introduction of thin cores for control of AC losses. Several cored cables have been fabricated for the latest generation HQ models using stainless steel and fiberglass cores. Coils have been fabricated using cored cables and will be assembled and tested in the near future.

### *Coil fabrication technology*

Several factors contributed to a steady improvement in coil fabrication procedures throughout the program. Different experiences and methods had to be compared and integrated in order to develop tooling and procedures that would be acceptable to all collaborating groups. Robust handling and shipping tools had to be devised to allow distributed coil production lines for the TQ, LQ and HQ models. Careful analysis was performed in relation to the scale up to 4 m length in the LR and LQ models. Nevertheless, a comprehensive modeling framework is not yet available, particularly in relation to the reaction process. The coil fabrication methods are still largely based on empirical knowledge and several iterations are typically needed to optimize new designs. A recent example is given by the development of the HQ models, in which excessive compaction during coil fabrication led to high rates of insulation failures in the first tests [22].

### *Quench performance and training*

The capability to approach the conductor limit in model magnets is an important indicator of the maturity of the technology, and the capability to reach the design point with minimal training and no retraining is an essential requirement for operation in the accelerator. On both fronts, positive results were obtained. The full conductor potential (based on critical current measurements of

extracted strands, without accounting for stress degradation) was obtained in the best SQ, LR, TQ and LQ models at 4.5 K, indicating that the design and fabrication process is well controlled and optimized. The best models also showed fast training and no retraining. However, in most cases several iterations were needed for a new design to achieve its full potential. The steady process of systematic analysis and improvement defines the success of an R&D program like LARP, but it is clear that more work is needed to achieve full control of this technology, in particular for what concerns the coil design and fabrication, and especially the reaction step.

### *Mechanical design and stress limits*

Providing adequate mechanical support in high-field magnets based on brittle superconductors requires structures that can generate large forces while minimizing stress on the conductor at all stages of magnet fabrication and operation. Consistent with the R&D goals of the program, the application of new concepts and advanced modeling capabilities was emphasized. In particular, a support structure originally developed at LBNL for high field dipoles [23] was applied to the LARP quadrupoles. This concept is based a thick aluminum shell, pre-tensioned at room temperature using water-pressurized bladders and interference keys. During cool-down, the stress in the shell increases due to differential thermal contraction relative to the iron yoke. This shell-based structure was evaluated against the more traditional collar-based structure in the TQ models, scaled-up to 4 m length in the LR and LQ models, and further optimized in the HQ models.

A series of tests were performed at CERN using the TQS03 models to better understand the Nb<sub>3</sub>Sn stress limits and its tolerance to a large number of cycles [24]. It was found that the magnet could perform satisfactorily up to 200 MPa average coil stress, which results in peak local stresses of the order of 250 MPa. This result considerably expands the engineering design space with respect to the 150 MPa level which was previously considered as the limit. In addition, a cycling test involving one thousand ramps from low to high field was performed, and no degradation was found.

### *Field Quality and Accelerator Integration*

Due to large beam size in the IR quadrupoles, their field quality plays a critical role on the beam dynamics during collision. Therefore, precise coil fabrication and structure alignment are required. Although early LARP magnets had limited alignment features, steady progress has been made and the last generation of HQ models incorporates full alignment at all steps of coil fabrication, magnet assembly and operation. No negative impact on mechanical support and quench performance resulting from the introduction of these features has been observed so far.

Field errors at injection are less critical, but need to be

carefully analyzed since Nb<sub>3</sub>Sn wires exhibit large magnetization due to high critical current density and large filament size. Compensation of persistent current effects by saturation of carefully designed iron inserts may provide an intermediate solution. Ultimately, wires with larger number of sub-elements should be developed to decrease the effective filament size.

Additional features will need to be incorporated in the magnet cold mass in order to successfully integrate the new IR quadrupoles in the cryogenic system of the LHC. A mechanical structure focusing on these requirements is currently under development and will be tested in future HQ models [25].

## SUMMARY

Intensive magnet R&D efforts are needed to meet the requirements of future colliders at the energy frontier. The LHC luminosity upgrade provides the opportunity to refine the results obtained in proof-of-principle Nb<sub>3</sub>Sn models and extend them to full-size production magnets suitable for operation in a challenging accelerator environment. The LARP program has made considerable progress in this direction, and is expected to complete the technology demonstration within the next several years. Successful construction and implementation in the high luminosity LHC will also provide a stepping stone for the application of high field magnet technology to next generation colliders, such as the High Energy LHC.

## ACKNOWLEDGEMENT

The results presented in this paper were obtained by LARP collaboration with support from the US DOE Office of High Energy Physics. A complete list of collaborators is available at URL <http://uslarp.org>.

## REFERENCES

- [1] F. Ruggiero (editor) et al., "LHC Luminosity and Energy Upgrade: a feasibility study", LHC Project Report 626, December 2002.
- [2] R. Kephart et al., "The US LHC Accelerator Research Program – A proposal", May 2003.
- [3] W. Sampson, S. Kiss, K. Robins, A. McInturff, "Nb<sub>3</sub>Sn Dipole Magnets", IEEE Trans. Magn., 15(1), January 1979.
- [4] J. Perot, "Construction and Test of a Synchrotron Dipole Model using Nb<sub>3</sub>Sn cable", IEEE Trans. Magn. 19(3), May 1983.
- [5] A. Asner et al., "Development and Successful Testing of the First Nb<sub>3</sub>Sn Wound, in-situ Reacted, High-Field Superconducting Quadrupole of CERN", IEEE Trans. Magn., 19(3), May 1983.
- [6] A. Asner et al. "First Nb<sub>3</sub>Sn Superconducting Dipole Model Magnets for LHC break the 10 Tesla Field threshold", MT-11, Tsukuba, Aug. 1989.
- [7] C. Taylor et al., "A Nb<sub>3</sub>Sn Dipole Magnet Reacted after Winding", IEEE Trans. Mag. 21(2), March 1985
- [8] A. den Ouden et al., "Application of Nb<sub>3</sub>Sn superconductors in accelerator magnets", IEEE Trans. Appl. Supercond. Vol. 7, 1997.
- [9] A. McInturff et al., "Test Results for a High Field (13 T) Nb<sub>3</sub>Sn Dipole", PAC-97, Vancouver, May 1997
- [10] A. Lietzke et al., "Fabrication and Test Results of a High Field, Nb<sub>3</sub>Sn Superconducting Racetrack Dipole Magnet", PAC-2001.
- [11] A. Lietzke, et al., "Test results of HD1b, an upgraded 16 T Nb<sub>3</sub>Sn dipole magnet", IEEE Trans. Appl. Supercond., Vol. 15, no. 2, pp. 1123-1127, June 2005.
- [12] High-Energy Physics Facilities of the DOE Office of Science Twenty-Year Road Map, HEPAP report to the Director of the Office of Science, 17 March 2003.
- [13] L. Rossi et al., High Luminosity Large Hadron Collider Design Study - HiLumi LHC, FP7-INFRASTRUCTURES-2011-1, November 2010.
- [14] R. Hafalia et al., "An Approach for Faster High Field Magnet Technology Development", IEEE Trans. Appl. Supercond., Vol.13, No. 2, June 2003, pp.1258.
- [15] P. Ferracin et al., "Development of a large aperture Nb<sub>3</sub>Sn racetrack quadrupole magnet", IEEE Transactions on Applied Superconductivity, vol. 15, no. 2, June 2005, pp. 1132-1135.
- [16] P. Ferracin et al., "Assembly and test of SQ01b, a Nb<sub>3</sub>Sn quadrupole magnet for the LHC Accelerator Research Program", IEEE Trans. Appl. Supercond., vol. 16, no. 2, June 2006, 382-385.
- [17] P. Wanderer et al., "Construction and Test of 3.6 m Nb<sub>3</sub>Sn Racetrack Coils for LARP", IEEE Trans. Appl. Supercond., vol. 18, no. 2, June 2008, pp. 171.
- [18] J. Muratore et al., "Test Results of LARP 3.6 m Nb<sub>3</sub>Sn Racetrack Coils Supported by Full-Length and Segmented Shell Structures", IEEE Trans. Appl. Supercond., vol. 19, no. 3, June 2009, 1212-1216.
- [19] S. Caspi et al., "Test Results of LARP Nb<sub>3</sub>Sn Quadrupole Magnets Using a Shell-based Support Structure (TQS)" IEEE Trans. Appl. Supercond., vol. 19, no. 3, Part 2, June 2009, 1221-1225
- [20] R. Bossert et al., "Fabrication and Test of LARP Technological Quadrupole Models of TQC Series", IEEE Trans. Appl. Supercond., vol. 19, no. 3, June 2009, pp. 1216-1230.
- [21] G. Ambrosio et al., "Test results of the first 3.7 m long Nb<sub>3</sub>Sn quadrupole by LARP and future plans", Proceeding of the 2010 Applied Superconductivity Conference, in press.
- [22] S. Caspi et al., "Test results of HQ01, a 120 mm 15 T Nb<sub>3</sub>Sn Quadrupole for the LHC Upgrade", Proceeding of the 2010 Appl. Supercond. Conference.
- [23] S. Caspi, et al., "A New Support Structure for High Field Magnets," IEEE Trans. Appl. Supercond. Vol. 12, No. 1, March 2002, pp. 47-50.
- [24] H. Felice et al., "Test results of TQS03, a LARP shell-based Nb<sub>3</sub>Sn quadrupole using RRP 108/127 conductor" Journal of Physics, in press.
- [25] J. Schmalzle et al., "Mechanical Design of an Alternate Structure for LARP Nb<sub>3</sub>Sn Quadrupole Magnets for LHC", this Conference.