



MgB₂ cables: design, manufacturing and assessment

K. Konstantopoulou, J. Hurte, P. W. Retz, A. Gharib, A. Ballarino




International Review of the Conceptual Design of the Cold Powering System
for HL-LHC Superconducting Magnets. CERN 3-4 July 2017

Outline

- Introduction
- Design parameters
- Experimental R&D assessment
 - Cabling at CERN
 - Tests and results
- Industrial cabling process
- Conclusions

Introduction: Problem statement


Design, for the first time, of a MgB_2 multi-cable assembly by using an *ex-situ* superconducting wire:

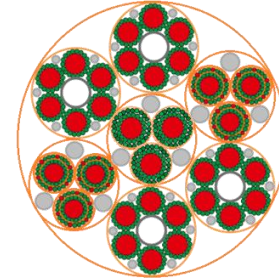

- Different sub-cables carrying currents up to 18 kA.
- Made with 1 mm MgB_2 reacted wire.
- Definition of the main cabling parameters: tensile load, twist pitch and bending radius.
- Complexity of the cabling process due to the electro-mechanical performance of the MgB_2 wire.


Introduction: Problem statement

MgB₂ multi-cable assembly

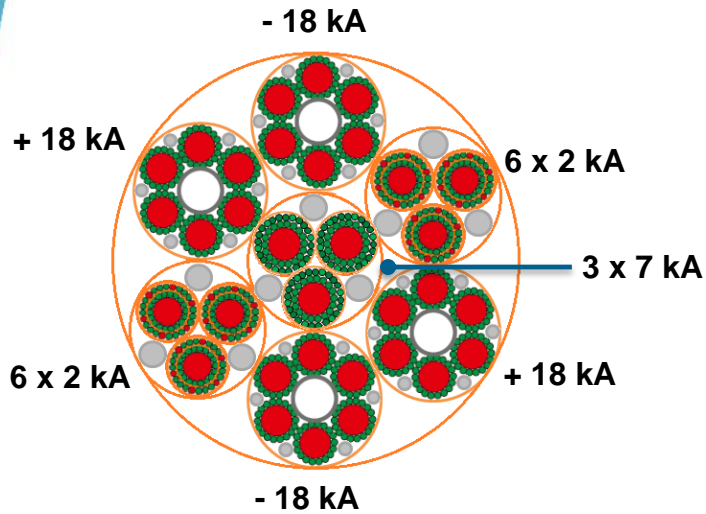


$\Phi \sim 75 \text{ mm}$

4 main sub-cables

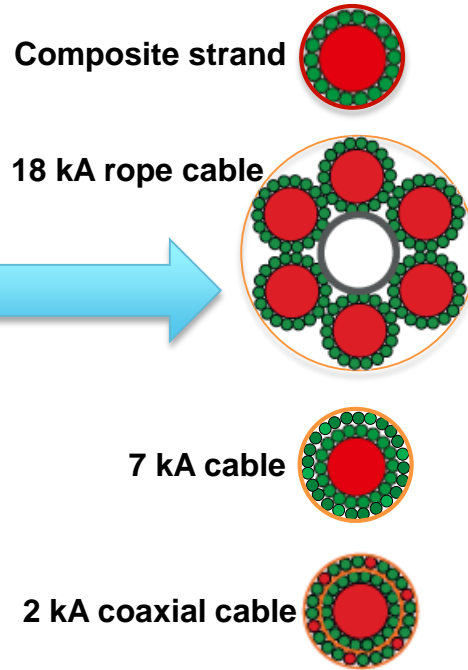

MgB₂ wire

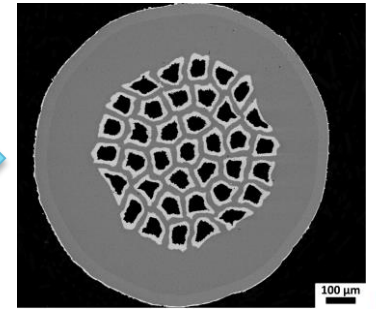

$\Phi \sim 1 \text{ mm}$

Introduction: Performed activities

- Electro-mechanical characterization of the 1 mm MgB₂ wire at RT and 4.2 K.
- Definition and evaluation of the main cabling parameters.
- Cable manufacturing and experimental validation.
- Overseeing of the industrial manufacturing.

Design parameters: MgB₂ wire critical strain

Motor system

Load cell
5 kN

- Purpose-built device

- ϵ_{crit} determination: no I_C degradation*



* No or negligible I_C degradation (<5%)

Tensile tests


ϵ_{crit} (%) at RT	ϵ_{crit} (%) at 4.2 K
0.26 ± 0.01	0.30 ± 0.01

Force transmission system & current leads

Sample holder

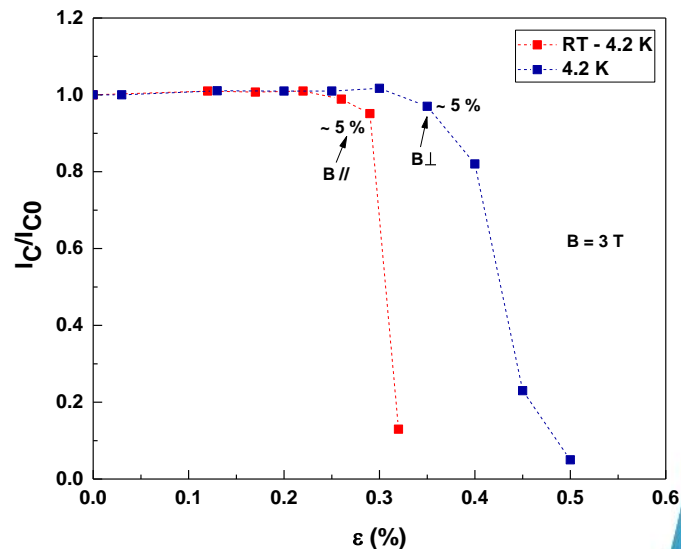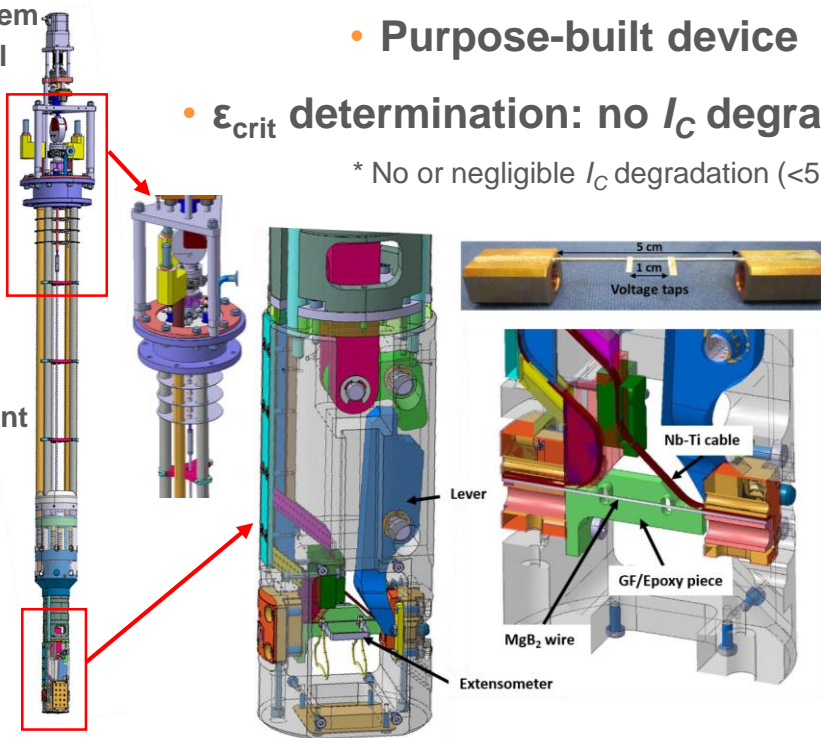


Mechanical characterization of the MgB₂ wire

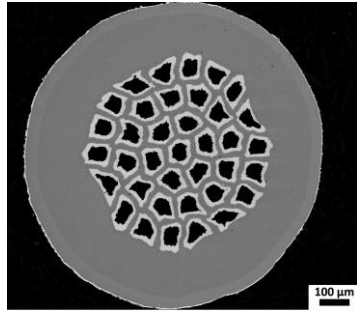


- Tensile tests at RT and at 77 K
- Single bending tests
- Triple bending tests
- Nanoindentation measurements

	MgB ₂	Nb	Ni	Nb-Ni	Monel	Cu
E (GPa)	97	103	207	230	179	118


1 mm wire	E (GPa)	$\sigma_{y, 0.2\%}$ (MPa)
RT	151 ± 2	244 ± 3
77 K	162 ± 1	323 ± 3

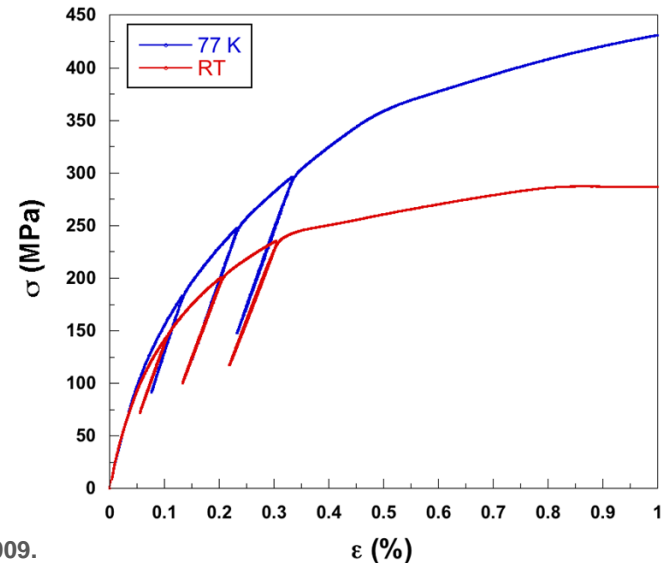

Design parameters: MgB₂ wire bending radius

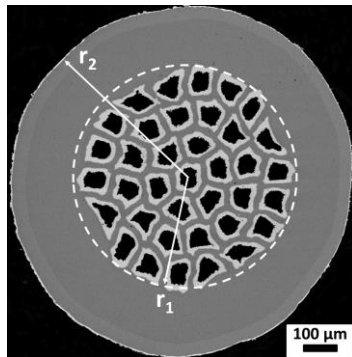

ϵ_t (%)	$\epsilon_t / \epsilon_{crit,RT}$	$R_{b,wire}$ (mm)
0.05	0.19	656
0.10	0.38	328
0.15	0.58	218
0.20	0.77	164
0.25	0.96	131
0.30	1.15	109

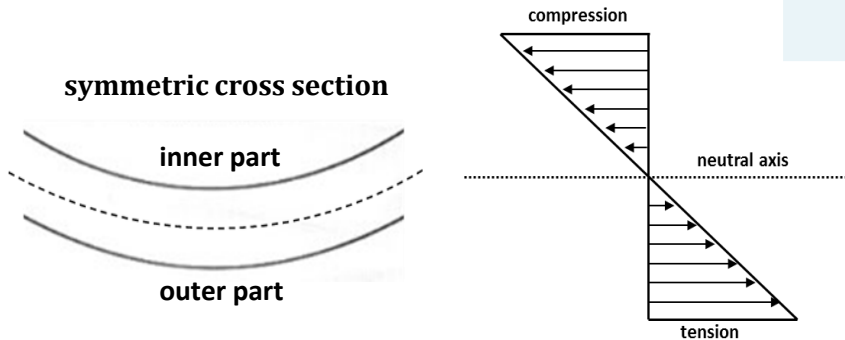


ϵ_t : tensile strain in the outer MgB₂ filaments.

$R_{b,wire}$: bending radius of the MgB₂ wire.

Konstantopoulou K. *et al.* 2016 Supercond. Sci. Technol. 29 084005.

Strain distribution

Design parameters: MgB₂ wire on “Composite strand” cable

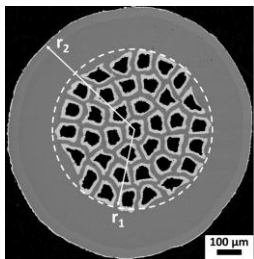


ε_t (%)	$\varepsilon_t / \varepsilon_{\text{crit,RT}}$	$R_{\text{b, wire}}$ (mm)	$T_{\text{p, wire}}$ (mm)
0.05	0.19	656	276
0.10	0.38	328	195
0.15	0.58	218	158
0.20	0.77	164	137
0.25	0.96	131	122
0.30	1.15	109	111

ε_t : tensile strain in the outer MgB₂ filaments.

$R_{\text{b,wire}}$: bending radius of the MgB₂ wire.

$T_{\text{p, wire}}$: twist pitch of the MgB₂ wire in the “Composite strand” cable.

Design parameters: proposed for sub-cables

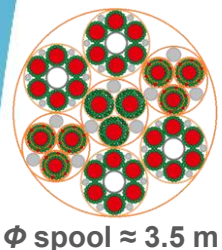




Φ spool \approx 3.5 m

	Wire/Cable	Φ (mm)	R_b (mm)	T_p (mm)		Tensile load (kg)
	MgB ₂ wire	~1.0	100	180	200	1.5 ± 0.5
	Composite strand	~7.5	300	600 – 800 - 1000		5 - 10
	18 kA rope cable	~24.0	550	1300		15 - 20
	7 kA cable	~10.5	400	600		10 - 15
	Triplet 7 kA coaxial cable	~23.5	550	-		15 - 20
	2 kA coaxial cable	~11.5	400	600		10 - 15
	Triplet 2 kA cable	~25.0	550	1300		15 - 20

The tolerance of the design parameters for the sub-cables is to be defined.

Experimental R&D assessment: cabling at CERN


- 25 configurations of “Composite strand” MgB_2 cables have been prepared at CERN to validate the cabling parameters.  Twist pitch = 160 – 400 mm.
- 1 configuration of “2 kA coaxial cable” has been prepared at CERN and tested in FRESKA test station. 
- 4 samples of “18 kA rope cable” have been prepared at CERN and measured at SM18. 

1 kN load cell



Cu core
 MgB_2 strands

$T_p = 170$ mm

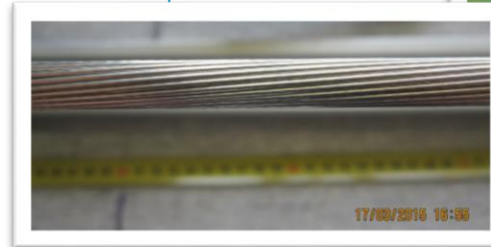

“Composite strand” MgB_2 cable

“2 kA coaxial cable”




$T_p = 200$ mm

Experimental R&D assessment: tests and results


- 1 m long “Composite strand” MgB_2 cables were bent around a spool of 400 mm diameter, without additional applied load (single and double bending).
- 3 m long “Composite strand” MgB_2 cables were bent around a spool of 600 mm diameter by applying tensile load of 10 kg per cable.



Spool diameter = 400 mm

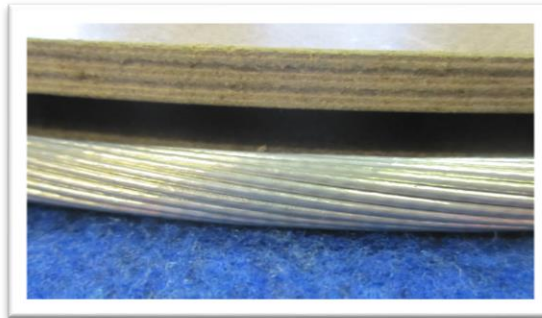


Spool diameter = 600 mm

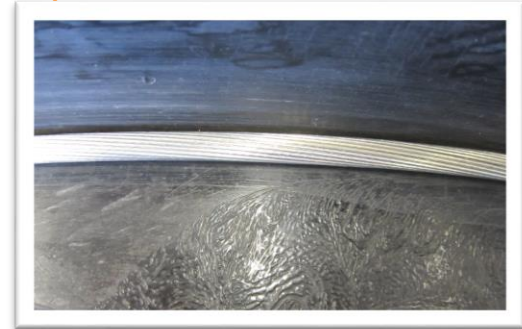


Experimental R&D assessment: tests and results

I_C measurement of “Composite strand” MgB₂ cable at FRESCA test station


Top splice

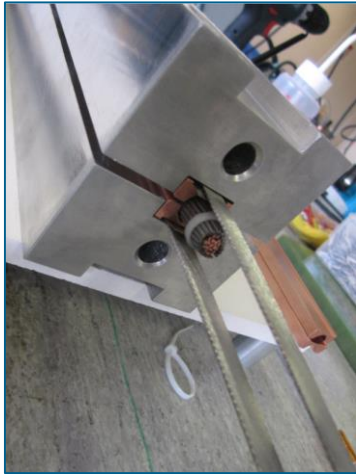

Bottom splice

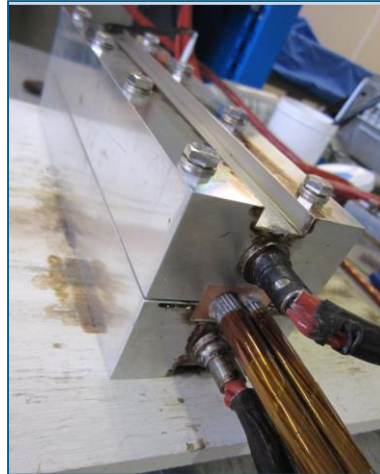

Support

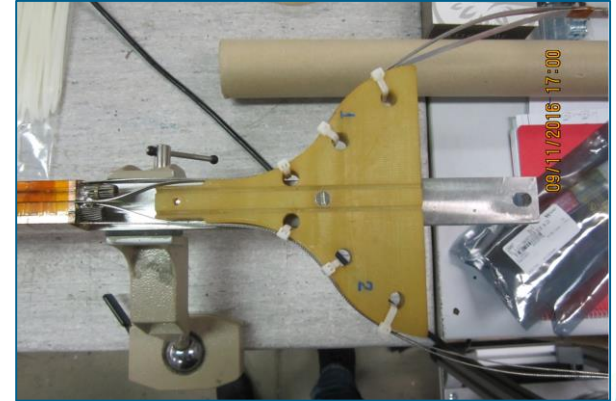


Experimental R&D assessment: tests and results


I_C measurement of extracted strands at 4.2 K and in 3 T parallel field.
No or negligible (<5%) I_C degradation was observed.



- The cable was bent without additional load.

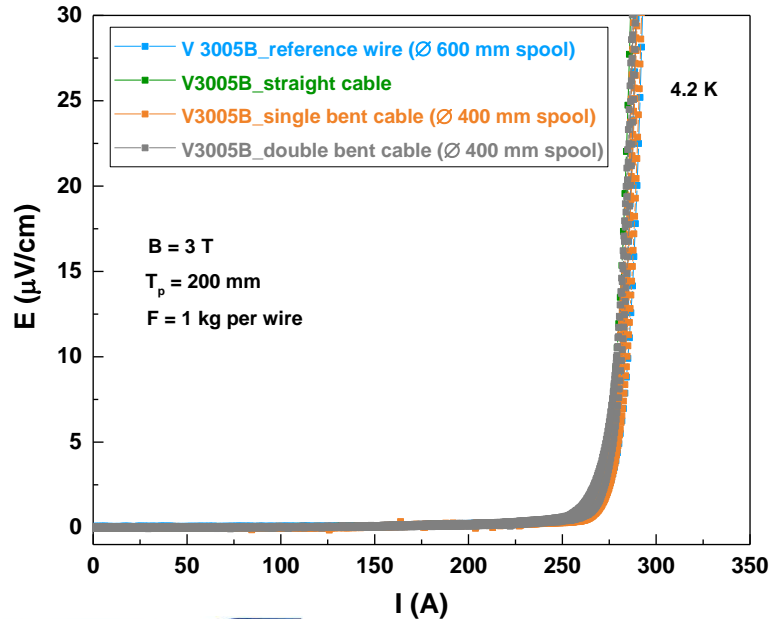


- The tensile load on the cable was 10 kg.

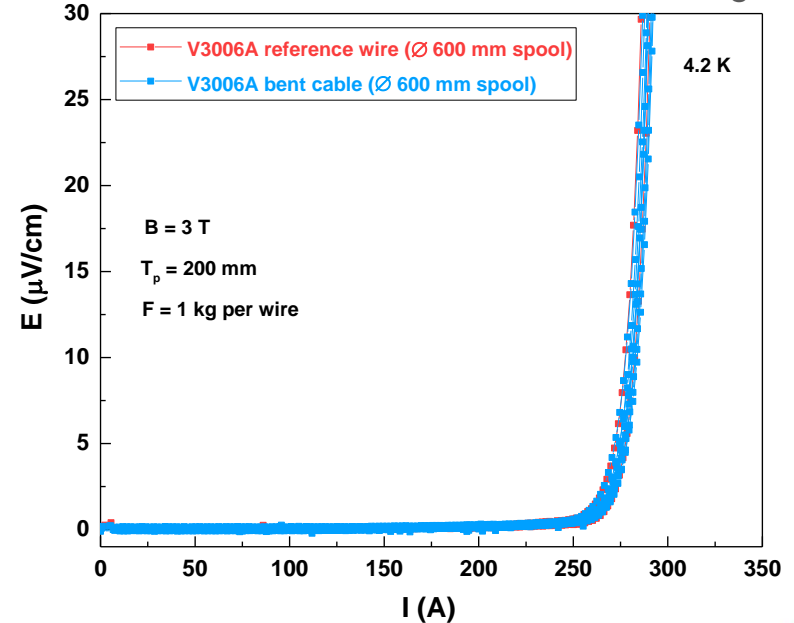


Experimental R&D assessment: tests and results

I_C measurement of MgB_2 cables at FRESCA test station and at SM18

“2 kA coaxial cable”

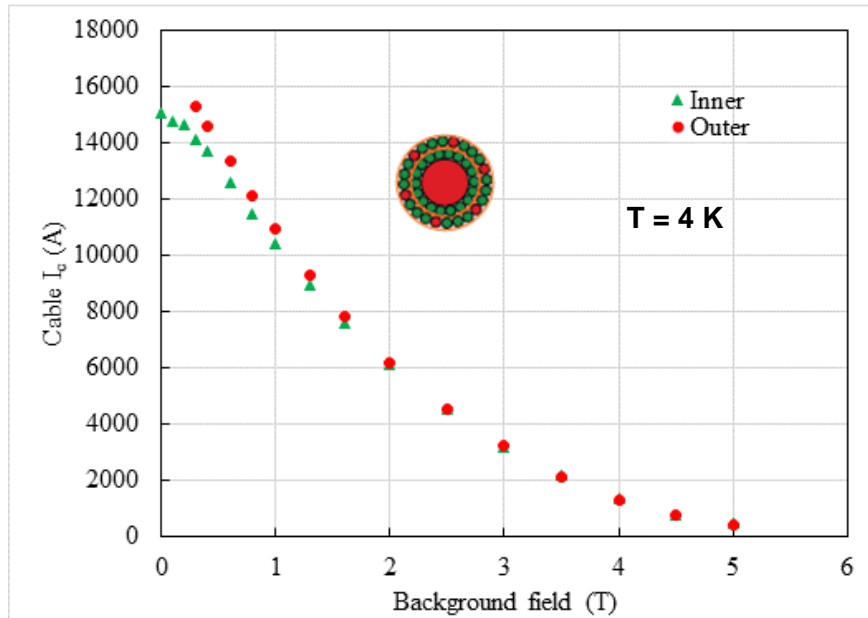

“18 kA rope cable”

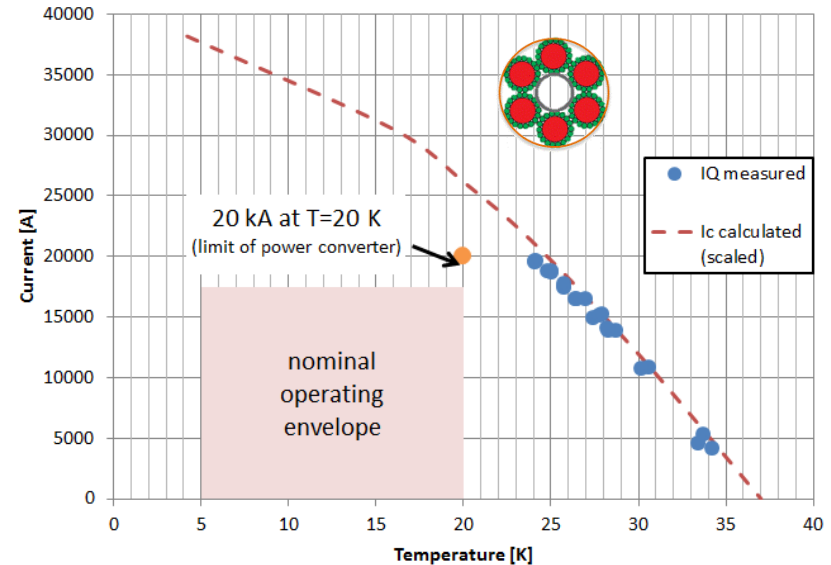


Giannelli S. *et al.* 2015 Internal Note 2015-03, EDMS Nr. 1476839.

Data by courtesy of J. Fleiter (CERN).

Experimental R&D assessment: tests and results

I_C measurement of MgB_2 cables at FRESCA test station and at SM18

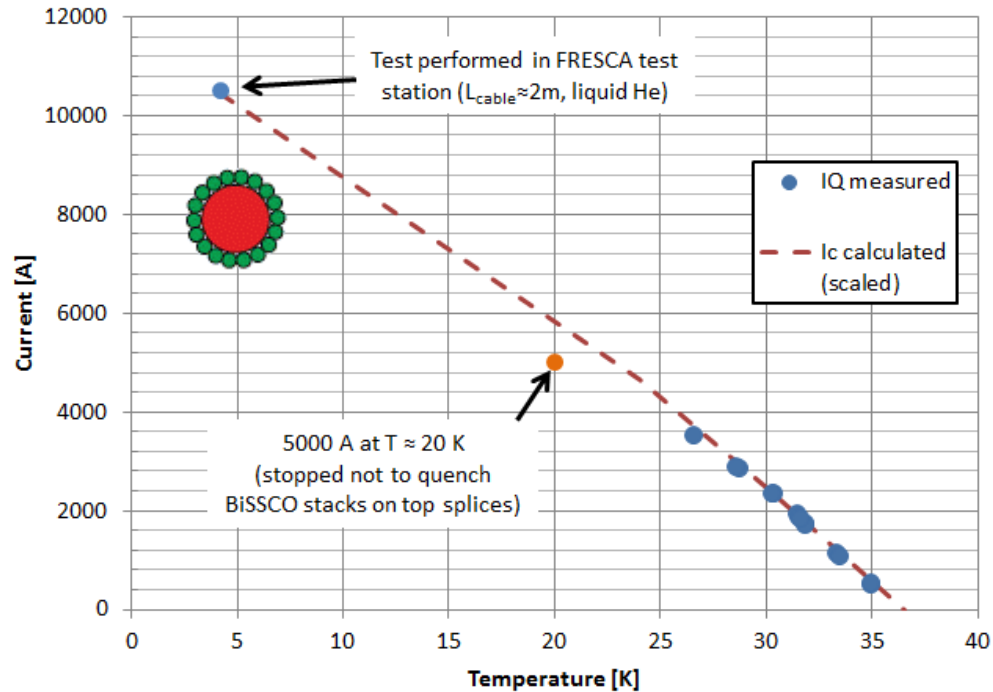

Giannelli S. *et al.* 2015 Internal Note 2015-03, EDMS Nr. 1476839.

Industrial cabling process: “Composite strand” MgB₂ cable

- The industrial manufacturing of “Composite strand” MgB₂ cables were carried out by TRATOS Cavi SpA (Italy), industrial partner and charter member of ICAS.
- **1st contract phase:** 12 samples “Composite strand” MgB₂ cables (6 straight and 6 bent) for the validation of the cabling process. The total length of the cables is 5 m.


“Composite strand” MgB ₂ cable	Tensile load per wire (kg)	T _p (mm)	ε _t (%)
SC sample #1	1.5	200	~ 0.09 < 0.2
SC sample #2	1.5	170	~ 0.14 < 0.2
SC sample #3	1.5	150	~ 0.18 < 0.2
SC sample #4	2.5	200	~ 0.11 < 0.2
SC sample #5	4.0	170	~ 0.16 < 0.2
SC sample #6	2.5	170	~ 0.15 < 0.2

All the bent
cables were
spooled on 450
mm diameter
spools.


Industrial cabling process: “Composite strand” MgB₂ cable






Cabling machine layout at TRATOS Cavi SpA.

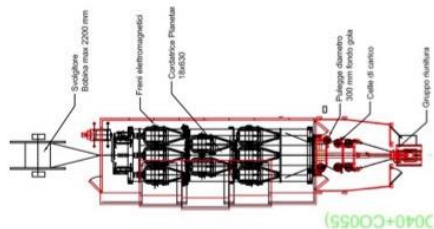

Cabling direction


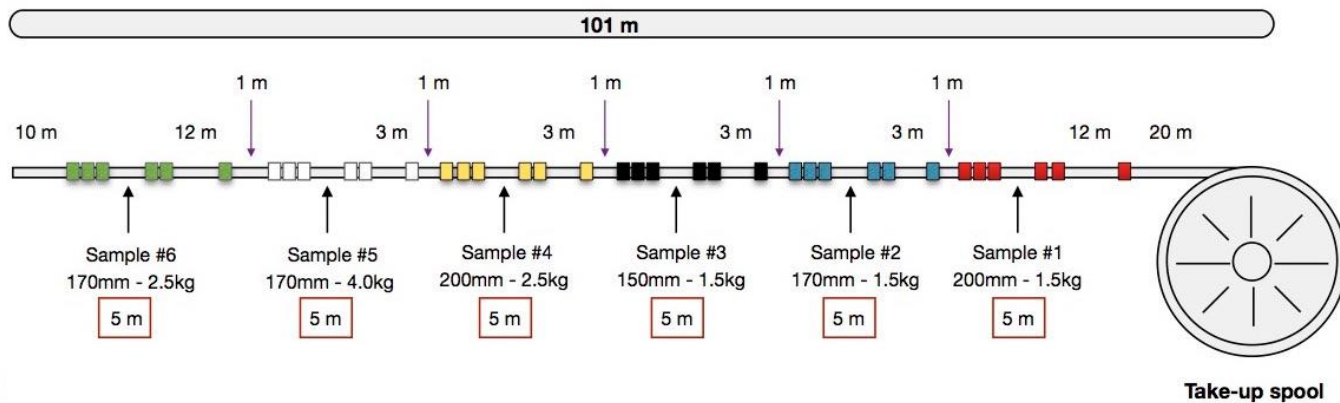


Industrial cabling process: “Composite strand” MgB₂ cable

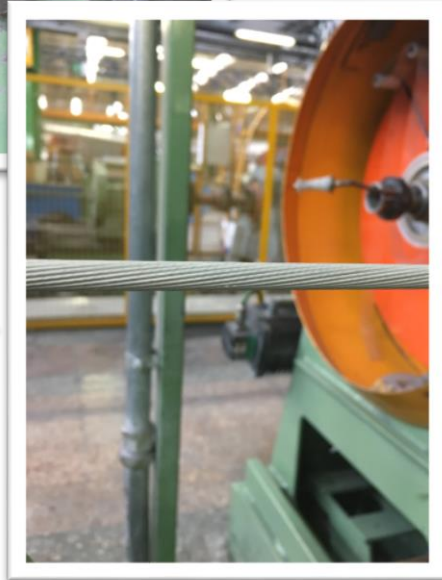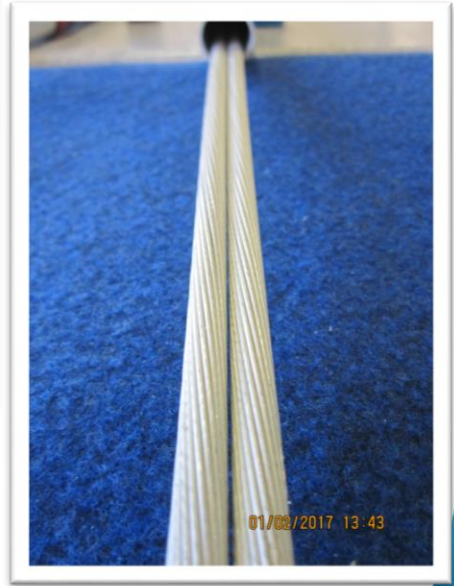

Experimental assessment at CERN


- The I_C of 135 extracted strands, from the received cables, was measured at 4.2 K and in parallel field up to 3 T.
- No or negligible (<5%) I_C degradation was observed when the tensile load per wire was 1.5 kg and twist pitch of 200 mm.

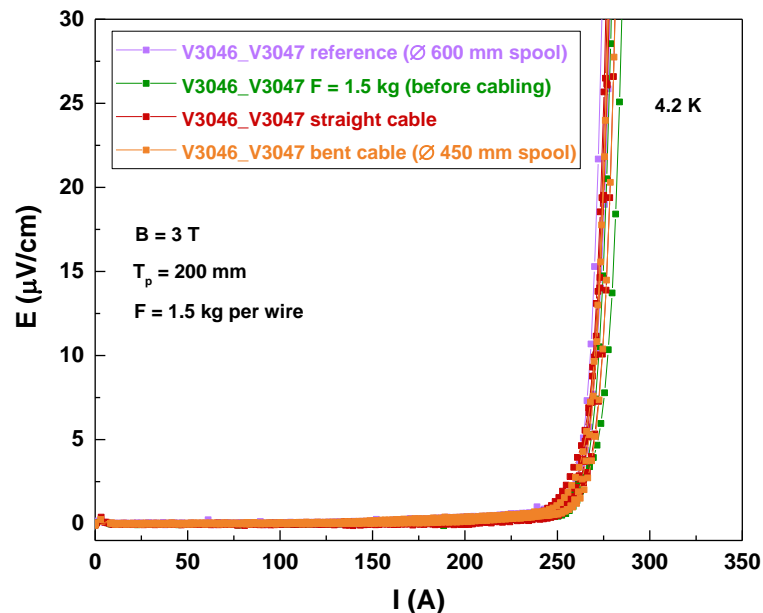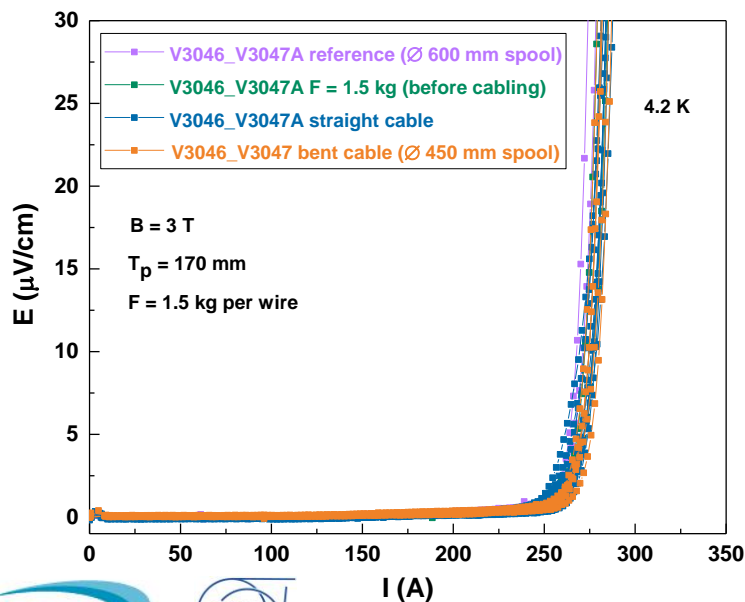

Experimental assessment at CERN



SC sample #1
 SC sample #2
 SC sample #3

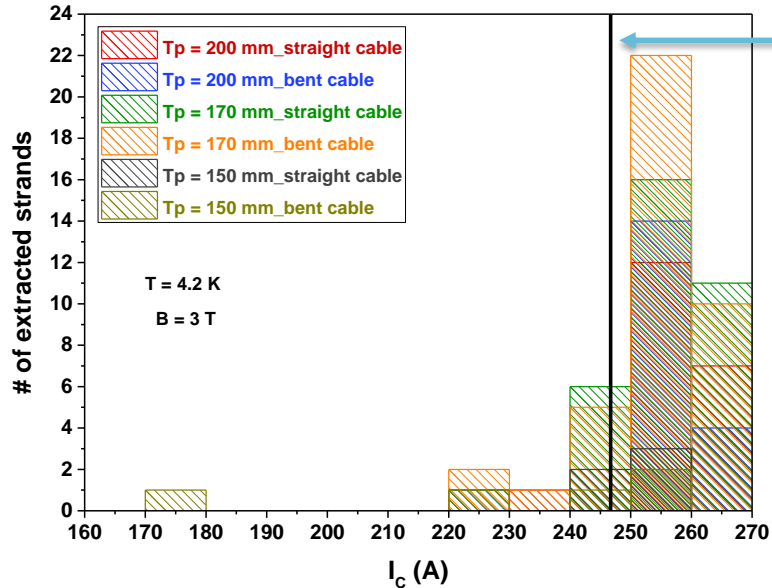

I_c degradation < 5%

“Composite strand” MgB ₂ cable	Tensile load per wire (kg)	T _{p, wire} (mm)	ε _t (%)	R _{b, cable} (mm)
25 m long	1.5	180	0.12 < 0.2	300

Industrial cabling process: 25 m long “Composite strand” MgB₂ cable




- 2st contract phase: One 25 m long “Composite strand” MgB₂ cable for the qualification of the long cabling process. The cabling parameters are: twist pitch of 180 mm, bending radius of 300 mm and tensile load per wire 1.5 kg.
- Single and double bending of a “Composite strand” MgB₂ cable on a 600 mm diameter spool.



Industrial cabling process: 25 m long “Composite strand” MgB_2 cable



- Shape recovery of a “Composite strand” MgB_2 cable after single and double bending.
 - No additional force was applied during the bending.

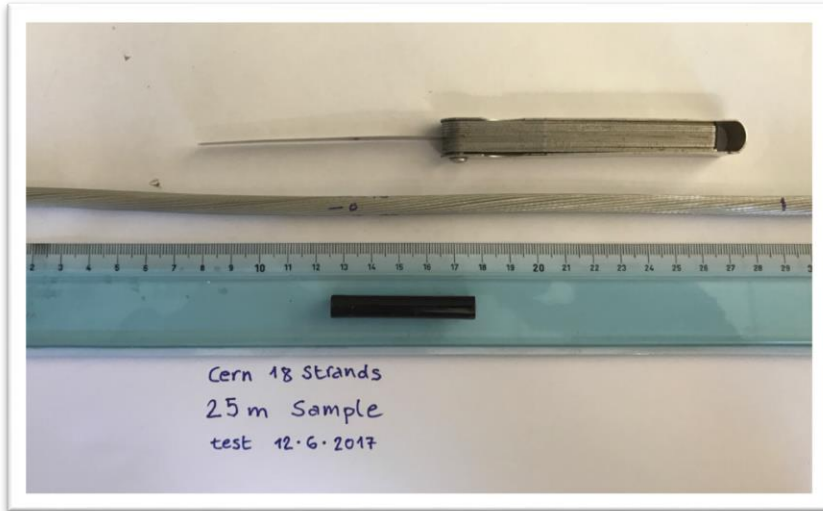

Industrial cabling process: upgraded machine

Cabling machine for “Composite strand”



Cabling machine for the bigger sub-cables.

Image: Confidential information

Conclusions (1/2)

- A thorough electro-mechanical characterization of 1 mm MgB₂ wire has been carried out at CERN for the determination of the adequate cabling parameters.
- Short length samples of “Composite strand” cables, “18 kA rope cable” and “2 kA coaxial cable” have been prepared and experimentally validated at CERN. I_C measurements of cables and extracted strands.
- The minimum *bending radius*, minimum *twist pitch* and maximum *tensile load* of the MgB₂ wire and cables have been proposed considering the geometry of each sub-cable and the mechanical performance of the MgB₂ wire at RT.

Conclusions (2/2)

- Twelve samples (straight and bent) of “Composite strand” MgB₂ cables have been manufactured by TRATOS Cavi SpA. and measured at CERN for the assessment of the cabling parameters and the industrial cabling process.
- A 25 m long “Composite strand” MgB₂ cable with *twist pitch* of 180 mm, *tensile load per wire* of 1.5 kg and *bending radius* of 300 mm has been manufactured and shipped at CERN, by TRATOS Cavi SpA.
- Experimental assessment at CERN of the 25 m long “Composite strand” MgB₂ cable.
- Specification for the “18 kA rope cable” and the “2 kA coaxial cable”.



Thank you for your attention

Acknowledgements: Many thanks to Sebastiano Giannelli, Jerome Fleiter, Jean-Eudes Maurice Duvauchelle, Alban Stimac, Jean-Sebastien Denis, Gerard Perrier Gros Claude, Pierre-Francois Jacquot, Anne Eychenne, Francis Beauvais and Bernardo Bordini.

