

Y. Onel^a, D. Winn^b

^aThe University of Iowa, Iowa City, Iowa • ^bFairfield University, Fairfield, Connecticut

Introduction

High precision timing is becoming an important issue in particle physics especially in Energy and Intensity Frontiers. Signals with FW10%-10% Max < 25ns and segmentation to handle >200 pileup(PU) are advantageous in many future Colliders and upgrades. Similarly tagged neutrino beams (from pions or muon factories) and tagged kaon beams would benefit from MIP rates exceeding 100's of MHz. The high track density and pile-up in high luminosity particle colliders are challenges for event reconstruction and analysis. MIP (minimum ionizing particle) pileup is a few percent in ~1x1 cm², 1200 cm radially along h=0. The case for adding a timing 4th dimension to calorimetry and tracking is becoming compelling.

Timing detectors must withstand 50 MRad and neutrons >3x10¹⁵n/cm². Timing has been shown by CMS and ATLAS to improve E_T miss resolution, and tag secondary vertices to ±few mm. Precise timing of calorimeter deposits and vertexes enable rejection of spurious data inconsistent with the primary vertex time. We discuss detectors for MIPs capable of timing precision to ±10's ps, and rate capabilities exceeding 100's of MHz.

Fast Scintillators for Precision Timing and High Rates

We discuss detectors for MIPs capable of timing precision to ±10's ps, and rate capabilities exceeding 100's of MHz. Issues for defining a Figure of Merit for timing scales as $\tau_{\text{decay}}/\sqrt{N}$ electrons, and the rate capability scales inversely as τ_{decay} . For optical transducers(SiPM, PMT, MCP-PMT), the timing precision is dominated by Trise and inversely by S/N. Noise in the experiments from low energy photons/x-rays scales inversely with X₀. SiPM and MCP-based detectors have risetimes shrinking to ~100-20ps.

Optical signals include scintillators with decay constants less than 2ns, Cherenkov radiators, and secondary emission detectors. Scintillators with high FOM include ZnO:Ga(GZO) (0.7ns decay), CdS:In (0.2 ns decay) and organic solid and liquid (with rad resistance) scintillators with decays less than 1 ns. We discuss scintillators, Cherenkov radiators(aerogels, quartz, Teflon AF, water, oils) and direct secondary emission MIP detectors as precision timing and high rate detectors.


Fast Scintillators for Precision Timing and High Rates

	ZnO:Ga (GZO)	CdS:In	EJ-232Q	Liq Scint A	CeBr ₃	LYSO
Light: γ/MeV	10,000-15,000	~3000-4,000	2900	1800	60,000	40,000
Decay (ns)	0.5-0.7	0.2	0.7	0.2	17	41-44
γ/MeV/ns	6,000	2,500	1,200	1500	1,700	740
T _{melt} (°C)	1,980	1,750	80	-10	722	2,050
dE/dx: MeV/cm	8.4	8.7	2	2.1	6.7	9.55
X ₀ (cm)	2.51	1.3	33	32	1.9	1.14
Peak λ (nm)	390-375	520	405	~400	371	420
Index n	1.85	2.53	1.6	1.55	1.91	1.82
Density (g/cc)	5.6	4.86	1	0.9	5.33	7.4

ZnO:Ga (GZO): ZnO:Ga is a very promising scintillator due to:

1. Rise and Fall Time: By contrast to LYSO, ZnO:Ga(1%-5%) has a rise-time 30-40ps vs 72ps LYSO, and a decay-time 0.5-0.7ns. $4 \sqrt{T_{\text{rise}}} \times \sqrt{T_{\text{fall}}}$ product ≤ 167ps, 10 times less than LYSO.

2. Large photon yield per ns per MeV: the highest of any known scintillator - ZnO:Ga produces more visible photons per ns than any other scintillator⁵, 7,000-9,000 photons/MeV/ns, at 375-395nm⁶, with total photons less than LYSO, but the peak photon pulse can be larger. There is no long glow.
3. Pileup is largely absent for ZnO:Ga compared to LYSO. A 90% integration time is <3ns (possibly lowering SiPM noise and reducing cooling requirements)with rate capabilities exceeding 100 MHz^{7,8}.
4. The radiation length of GZO is 2.2 times larger than LYSO. For MIP-detecting tiles, this means that fewer low energy gamma and x-rays will convert in the tiles, lowering background and noise rates.
5. Energy loss per mm and an index n are comparable to LYSO. A 1 mm thick layer of ZnO:Ga produces >1200 photons over 500-700ps.
6. Doped-ZnO is very rad-hard⁹ (as are most metal oxides) – it was used as a fast phosphor in e-beam gadgets. As a CRT phosphor it has >1GRad resistance (25 KeV electrons) (LYSI~10 MRad).

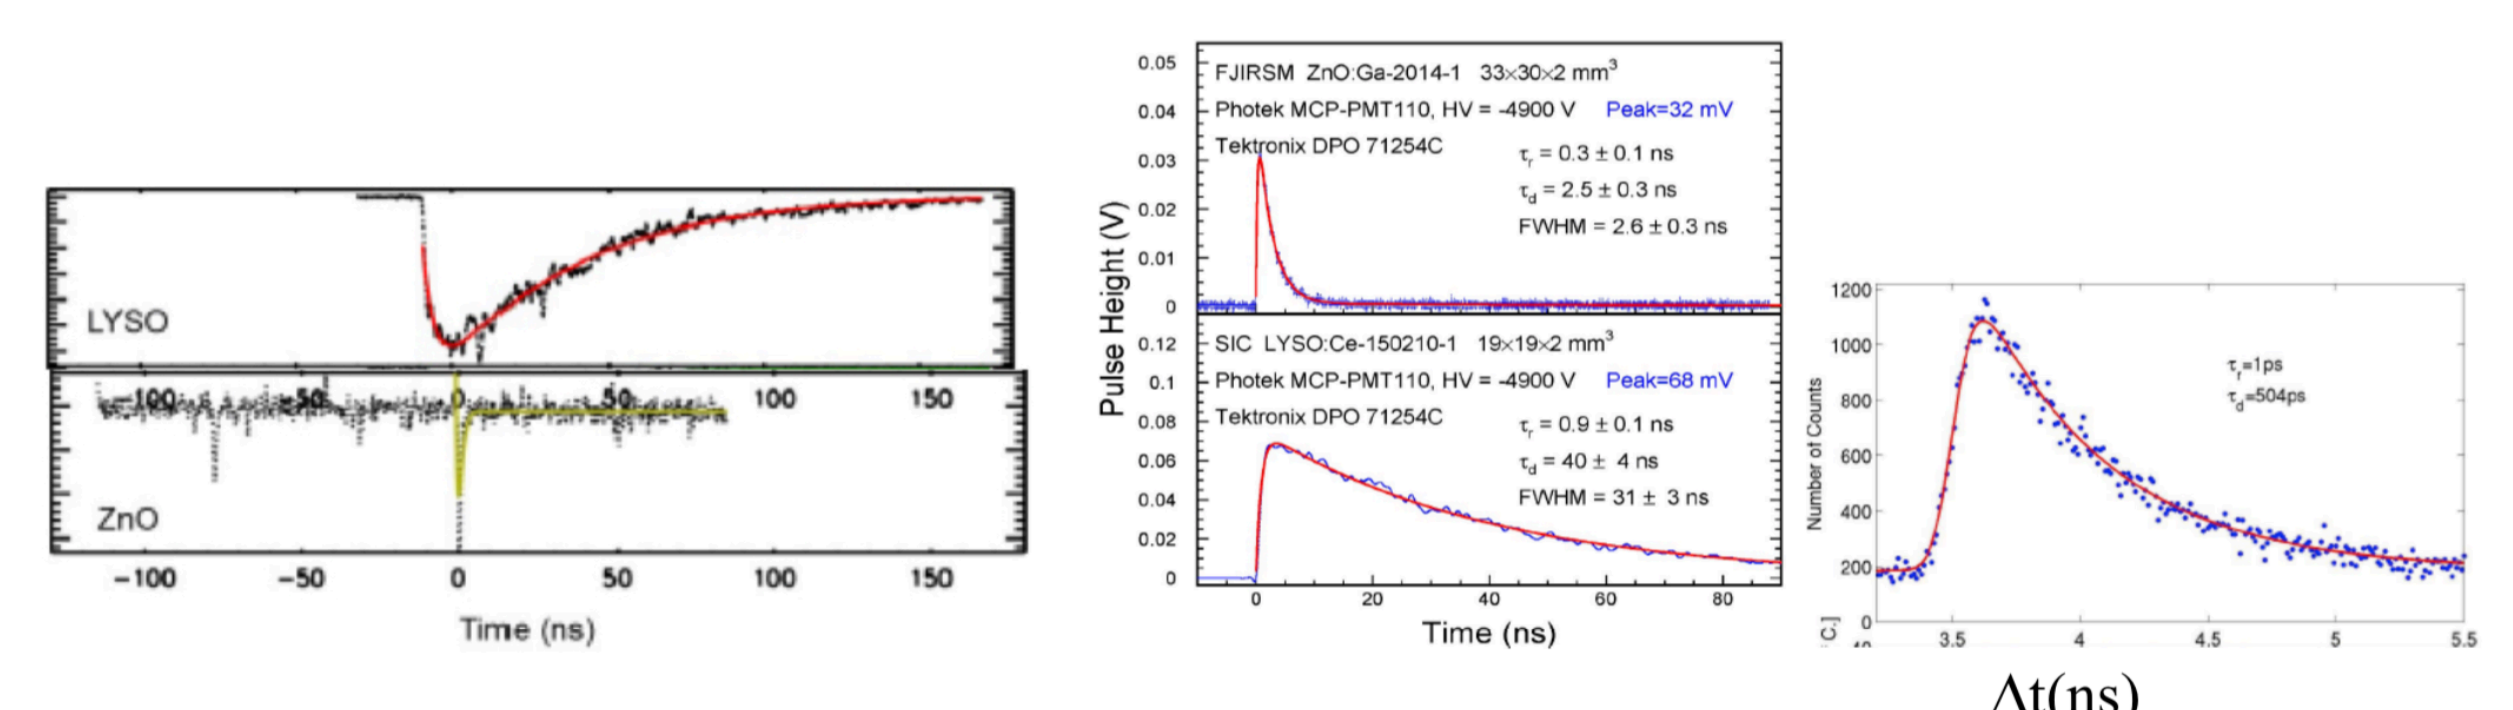

(L)Comparison of LYSO and ZnO:Ga flash-X-ray pulse shapes using a 20 GHz bandwidth 100 GHz sampling oscilloscope (y-axis arbitrary scale) using a fast MCP-PMT¹⁰. M: x-ray stimulated ZnO:Ga emission compared using an MCP-PMT and oscilloscope through 10 m cables.¹¹ R: pulse shape from a ~1 mm thick polystyrene disc loaded with 10% ZnO:Ga nanopowder with a 504 ps fitted decay.¹² Note: small variations in timing and peak signals are due to different photodetectors, DAQ, and ZnO:Ga doping levels. MIP data is essentially the same, the decay times varying between 0.5-0.7 ns for different samples.