



Modeling quench propagation in the ENEAS HTS CICC

A. Zappatore¹, A. Augieri², R. Bonifetto¹, G. Celentano², L. Savoldi¹, A.
Vannozzi² and R. Zanino¹

¹NEMO group, Dipartimento Energia, Politecnico di Torino, Torino, Italy

²ENEA Frascati Research Center – Superconductivity Laboratory, FSN
Department, Frascati, Italy



Outline




- Roadmap of our HTS magnet modeling effort
- Aim of this work
- The ENEA HTS CICC
- Preliminary analysis
- 1D model description
- Results
- Conclusions and perspective

H4C roadmap

Target: to develop an **HTS magnet model**
First, an **HTS CICC model** needs to be developed

Preliminary analysis to guide the development of the 1D CICC model [1]
[1] A. Zappatore et al., SuST 32(8), 2019

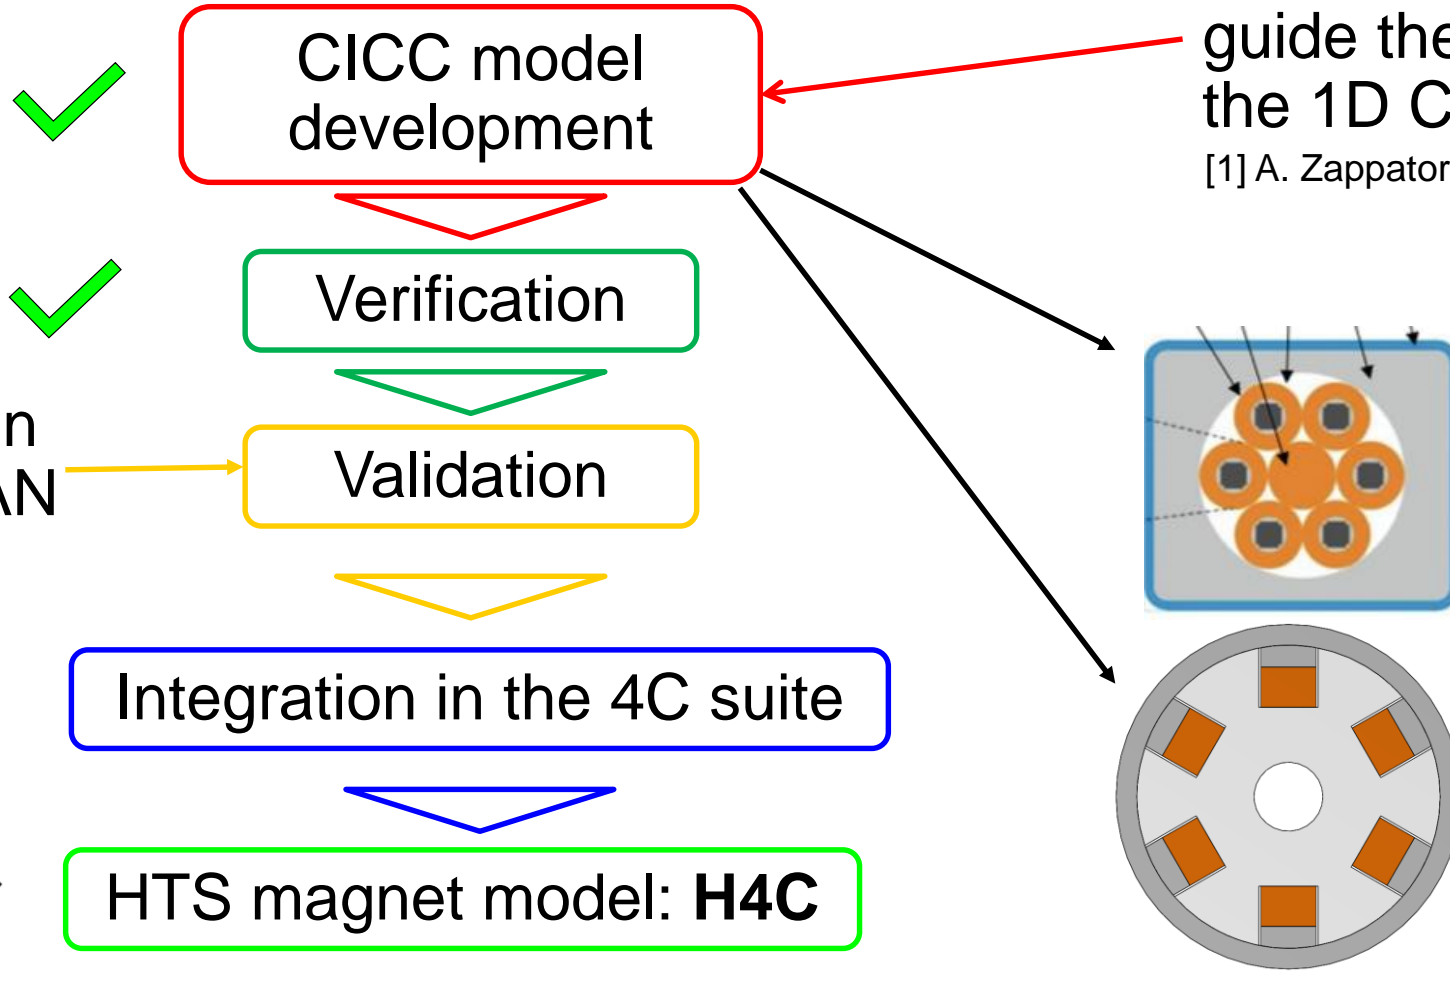

Presented at
CHATS2019
(KIT HTS CICC)

Here focus on
ENEA HTS CICC



Aim of this work


- Develop a 1D model of the ENEA HTS CICC
- Calibrate the free model parameters through dedicated experiments
- Apply the 1D conductor model to the analysis of quench propagation in the ENEA HTS CICC

The ENEA HTS CICC

6 slots (4.3 mm x 4.3 mm) equipped with 20 REBCO non-soldered 4-mm-wide tapes each

Side channels in each slot

5 mm ϕ central hole for SHe cooling

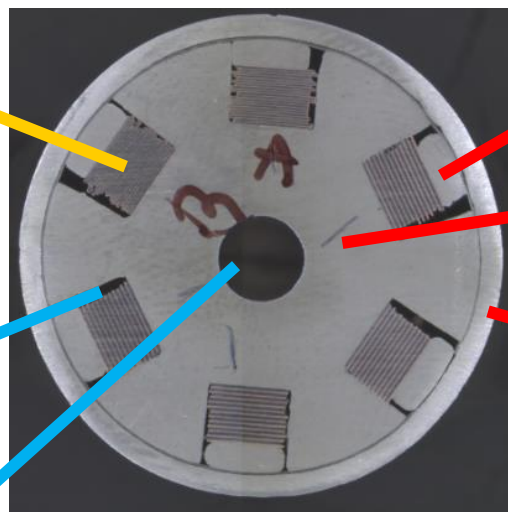


22 mm

Aluminum filler to hold the HTS stack in position

Aluminum core with twisted slots

Aluminum round jacket 1.5 mm thick

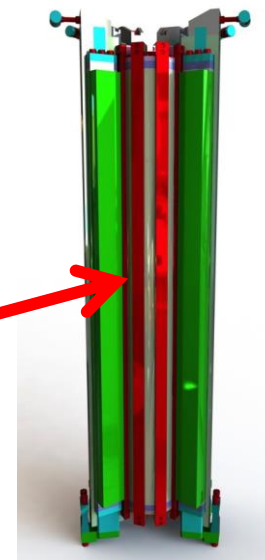

Application in the medium term: HTS CS insert for the Divertor Tokamak Test (DTT) facility currently under design in Italy

Preliminary analysis

Aim: understand qualitatively if LTS 1D codes (key feature: uniform T and J on the cross-section) for TH analysis are OK also for HTS CICC

Fluid model

$$Pe = Re Pr \gg 1$$



For SHe flow modelling a **1D** model along the conductor is sufficient



Solid model

$$Bi_{\text{stack}} > 1, Bi_{\text{core}} > 1$$



For thermal modelling of the cross section 1 region (as in LTS TH models) is NOT sufficient



Detailed model of the cross-section to obtain guidelines for the development of the CICC model [1]




[1] A. Zappatore et al., *SuST* 32(8), 2019

Detailed 0D+2D electro-thermal model of the CICC cross section

Aim of the detailed model: understand how different regions of the conductor cross-section can be lumped to develop a 1D conductor model (along)


2D Thermal

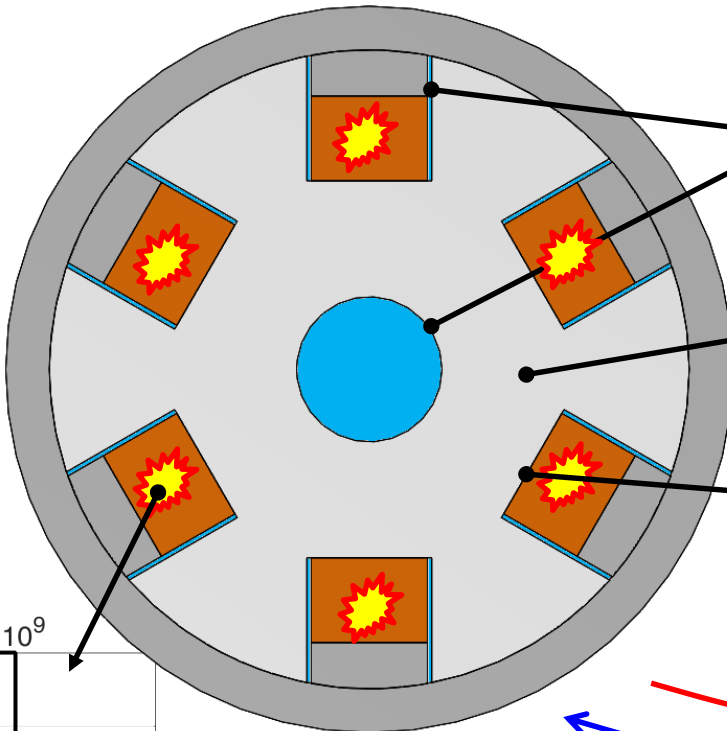


Convection with He at
 $T=4.5 \text{ K}$, $h=5000 \text{ W}/(\text{m}^2\text{K})$

Heat conduction
in solids

Thermal contact
resistance

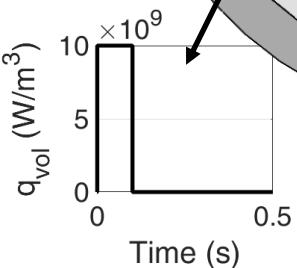

0D Electric

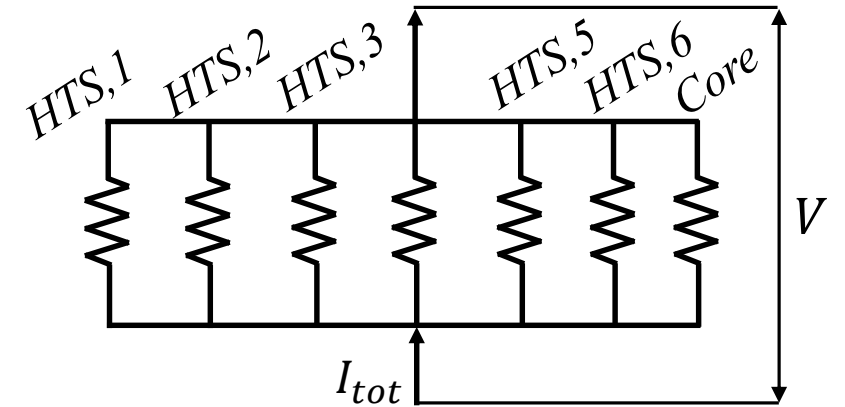


$$\begin{cases} V = R_{Al} I_{Al} \\ V = V_C \left(\frac{I_{HTS,i}}{I_{C,i}(B,T)} \right)^n \\ I_{tot} = I_{Al} + \sum_{i=1}^{N_{Stack}} I_{HTS,i} \end{cases}$$


T

$q_i = R I_i^2$

Results

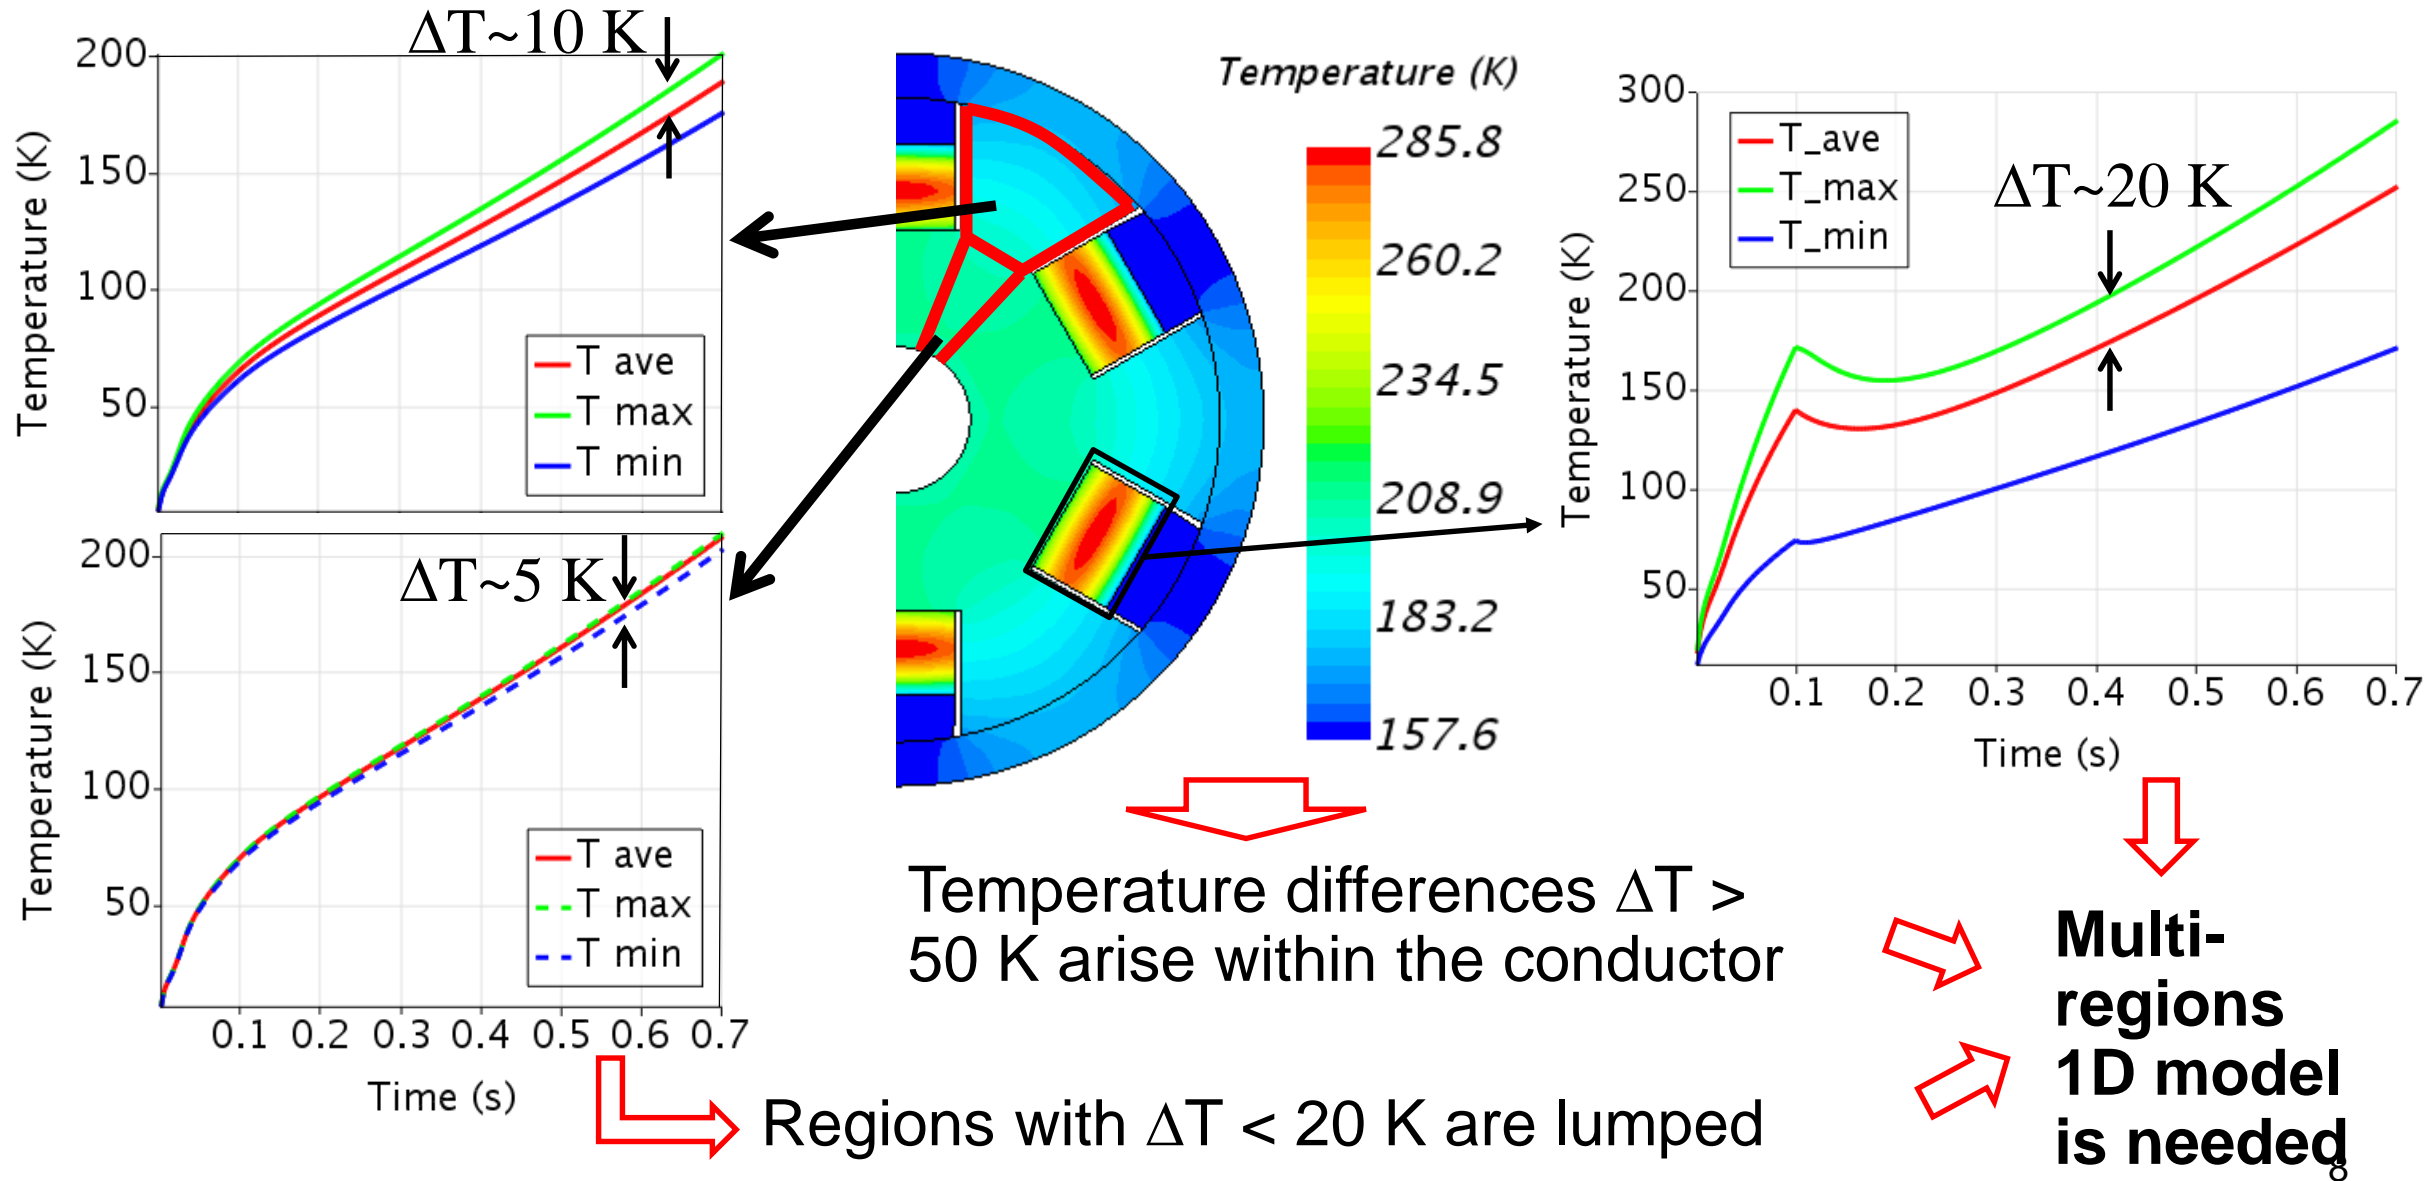

1D thermal + hydraulic + electric model

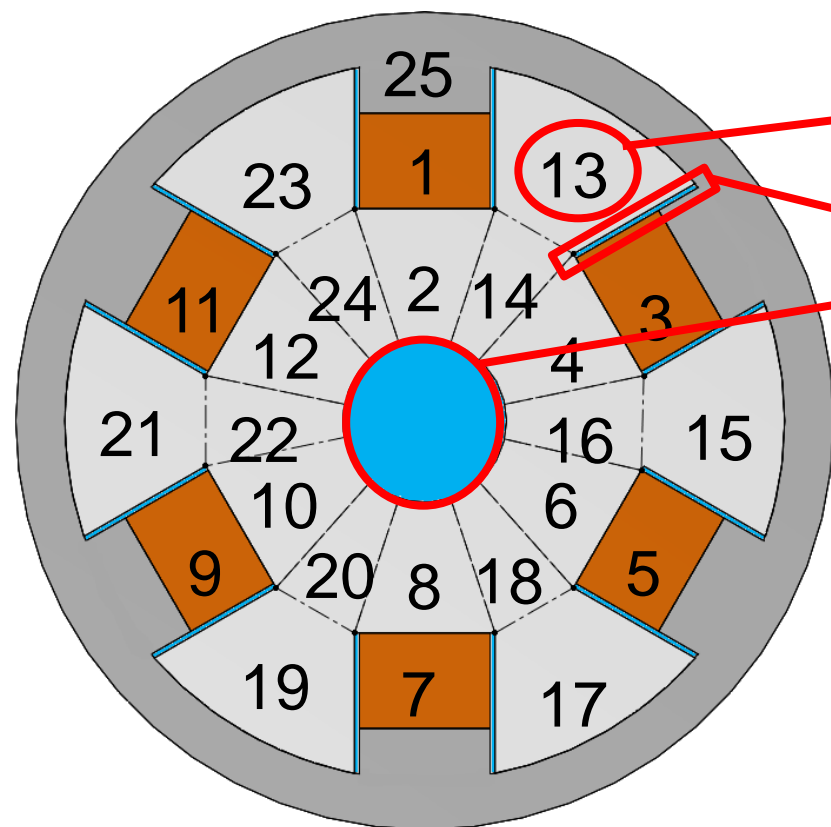

- Heat conduction in solids (25 regions)
- Euler-like set of PDEs for SHe speed, pressure, temperature (13 regions)
- Diffusion-like equation for the current along the different solids (25 regions)

Thermal model

Fluid flow model

Electric model


Op. condition

$T_{\text{He}} = 4.5 \text{ K}$

$L = 132 \text{ m}$

$B = 17.1 \text{ T}$

$I = 32 \text{ kA}$


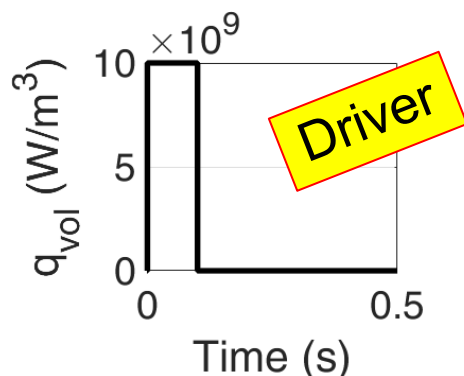


Interfaces

- Solid – solid
 - Thermal
 - Core – jacket: $11400 \text{ W}/(\text{m}^2\text{K})$ [2]
 - Core – stack: $32000 \text{ W}/(\text{m}^2\text{K})$ [2]
 - Electric
 - Linear resistance: $0.4 \text{ m}\Omega/\text{m}$ **[exp.]**
- Solid – fluid: heat transfer coefficient **from CFD**

[2] Y. A. Cengel, *Fundamentals of Thermal-Fluid Sciences*, 2017


Results (I)

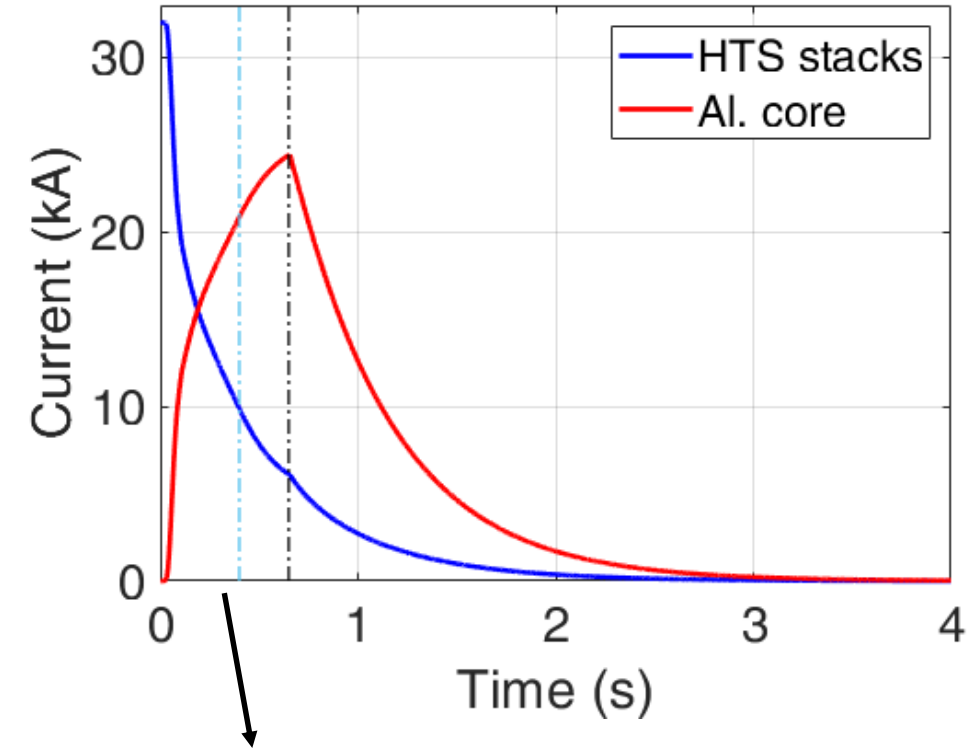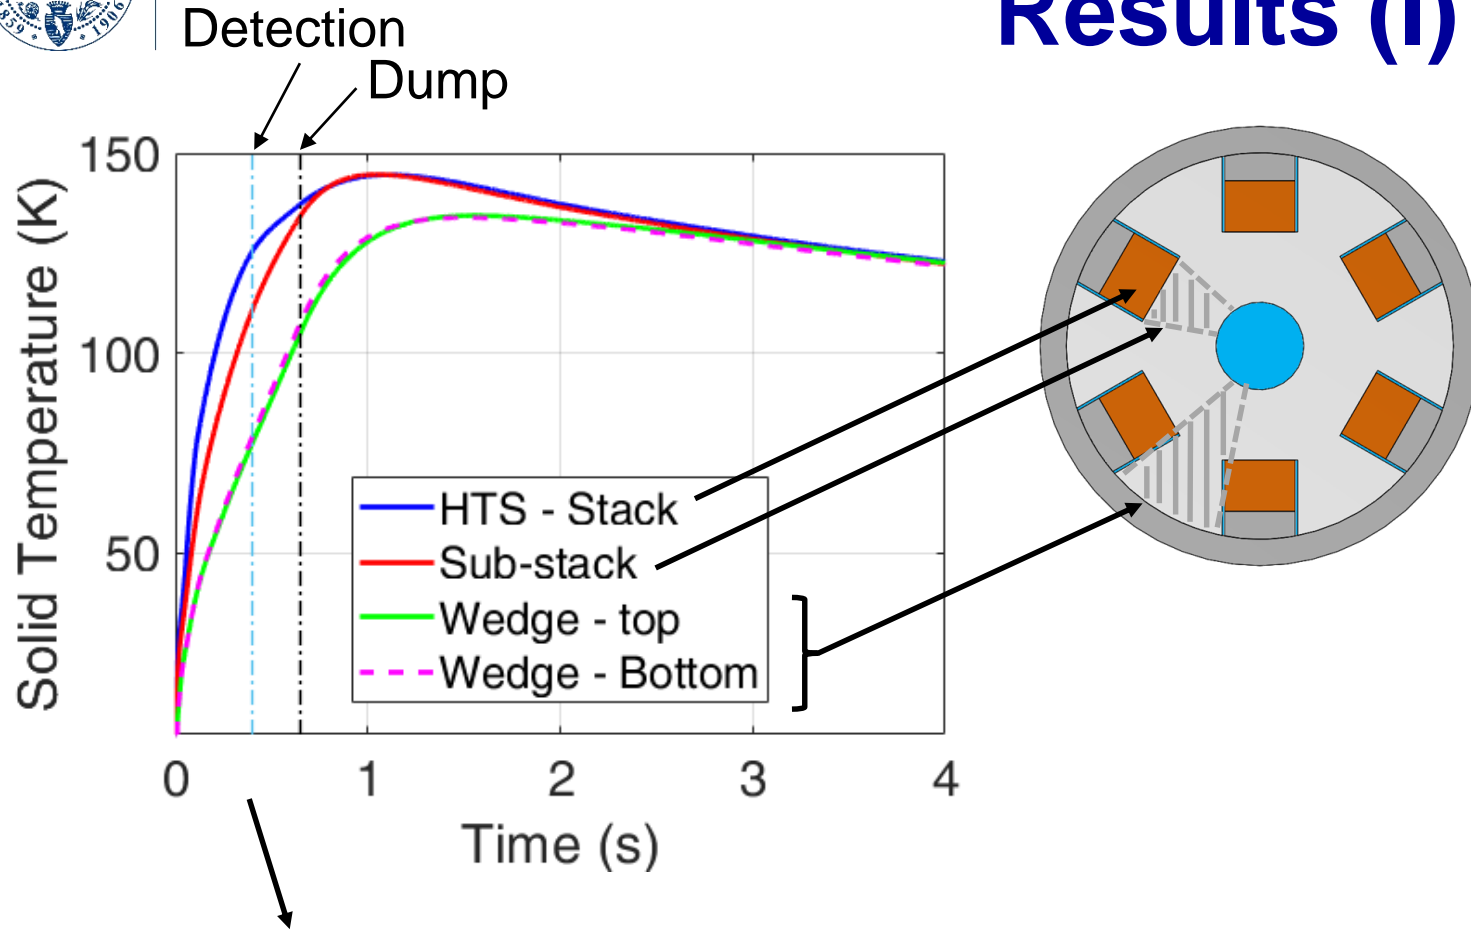


Temperature differences between stacks and core > 40 K \rightarrow issues on thermal stresses to be addressed in the future

- Inter-slot resistance low enough to guarantee current redistribution from the HTS stacks to the core
- Before the dump, the aluminum core arrives to carry most of the current, due to temperature increase in the tapes stabilizer

Results (II)

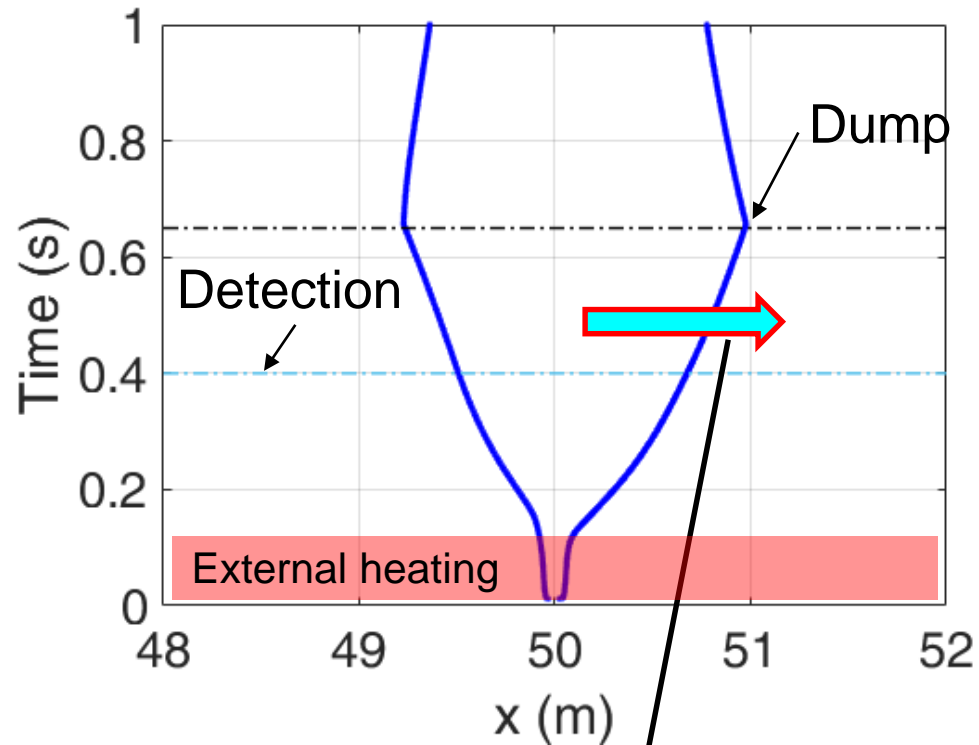

Hot He helps propagating the quench downstream

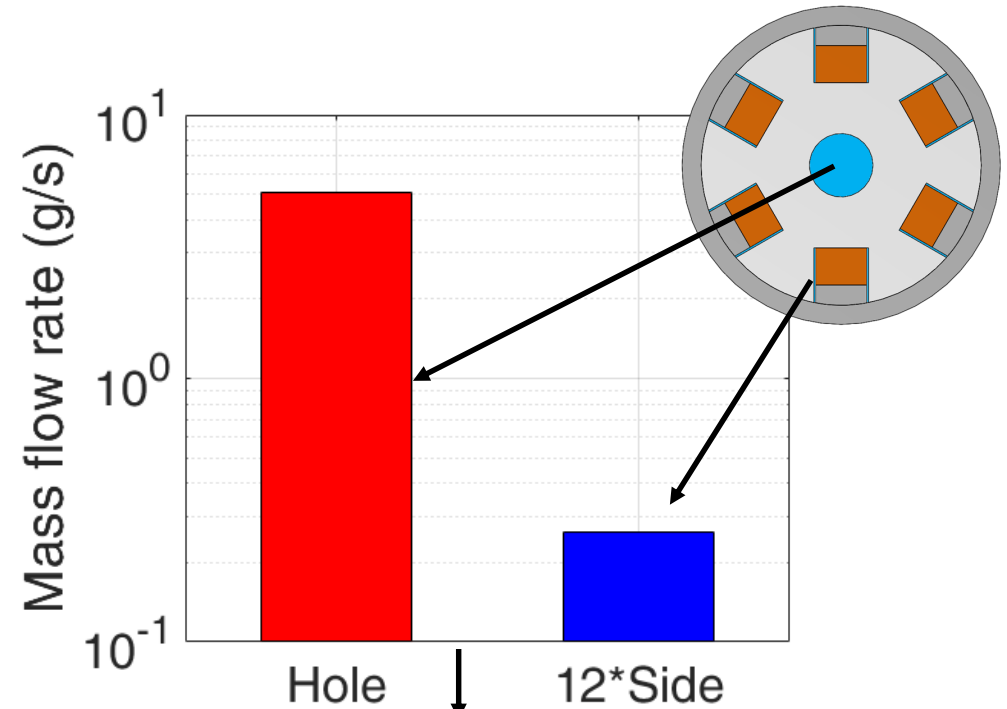


Total dm/dt in side channels
 $\sim 1/20$ dm/dt in hole

Limited cooling capabilities
of He flow in side channels

Results (III)

- The DTT CS will have delay time (τ_{delay}) = 2 s and current discharge time (τ_{dis}) = 4 s **BUT**
- τ_{delay} and τ_{dis} for the CS insert are still an open issue in the design

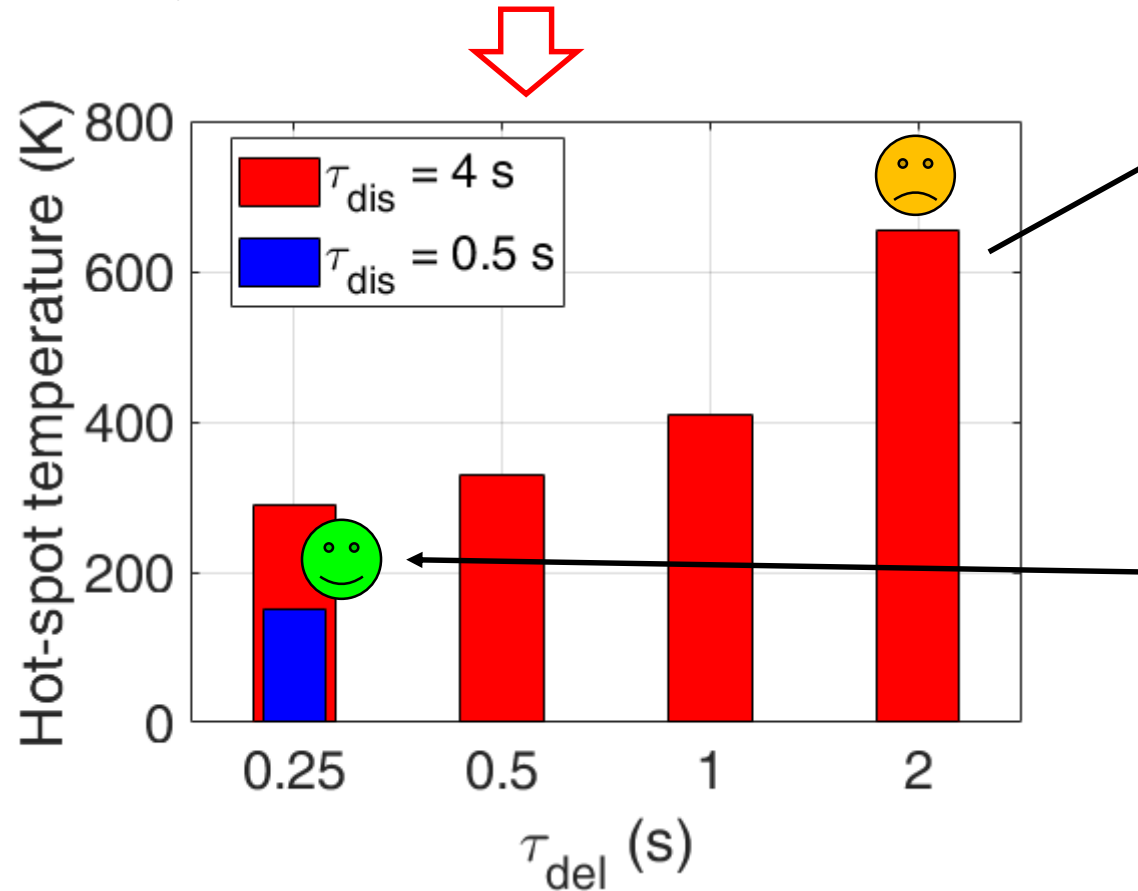

Same τ_{dis} for CS and insert \rightarrow too high hot-spot temperature

- Warning bell for quench propagation and current dump in an HTS magnet
- Foresee different strategy for the discharge of the CS insert



Conclusions and perspective

- A 1D thermal-hydraulic-electric model has been developed and applied to the analysis of quench propagation in the ENEA HTS CICC
- The model shows that
 - Large temperature differences arise in the CICC cross-section
 - The current redistributes from the stacks to the slotted core
- The delay time for the quench detection in the DTT CS insert coil and the current discharge time should stay below 0.5 s, otherwise the hot-spot temperature becomes too high
- In perspective, the CICC model will be:
 - validated against the quench tests foreseen in 2020 @ SULTAN
 - embedded in the H4C magnet model (which already includes winding pack, coil casing and cryogenic circuit) to analyze the performance of an HTS magnet